


DE GRUYTER
OPEN

GOSPODARKA SUROWCAMI MINERALNYMI – MINERAL RESOURCES MANAGEMENT

2016 Volume 32 Issue 4 Pages 5–28
DOI 10.1515/gospo-2016-0036

STANISŁAW Z. MIKULSKI,* REGINA KRAMARSKA**, GRZEGORZ ZIELIŃSKI***

Rare earth elements pilot studies of the baltic marine sands enriched in heavy minerals

Introduction

The use of a number of elements that rarely formed economic deposits, but they are of major importance for the economy of the countries in the European Union is of key importance in modern industrial production. The rare earth elements (REE), which were considered critical for the economic development of the most developed countries of the EU are among these elements (Opinion 2006; Galos and Smakowski 2008; EU Resolution 2011; Moss et al. 2011; Smakowski 2011; Szamałek 2011; Galos et al. 2012). The most important among the latest REE technologies are: lanthanum, europium, erbium and neodymium (Chakhmouradian and Wall 2012; Haque et al. 2014; Paulo and Krzak 2015).

In recent years, the global production of rare earths oxides (REO) has been at the level of the 123–124 thousand tons/year (Smakowski et al. 2012; USGS minerals, 2016). The rare earth metals market is controlled by China, which has the world's largest resources (> 20%; approx. 55 million tons) and annually provides more than 95 percent of the demand for rare earth materials (Hatch 2012). Chinese restrictions in the export of REE over the past few years have led to international concerns about future supply shortages

* Ph.D., D.Sc., Assoc. Prof., Polish Geological Institute-National Research Institute, Warszawa, Poland;
e-mail: stanislaw.mikulski@pgi.gov.pl

** Ph.D., Polish Geological Institute-National Research Institute, Marine Geology Branch, Gdańsk-Oliwa,
Poland; e-mail: regina.kramarska@pgi.gov.pl

*** Ph.D., Polish Geological Institute-National Research Institute, Warszawa, Poland;
e-mail: grzegorz.zielinski@pgi.gov.pl

([Klupa 2012](#)). Despite this fact, the world REE resources are giant (about 130 million tons REO; USGS minerals, 2016) and sufficient to cover the current volume of demand for more than 1,000 years.

Minerals that contain REE occur in the form of primary and secondary concentrations in several genetic types of deposits ([Paulo 1999](#)). The most important among the primary deposits are those related to alkaline magmatic complexes and carbonatites ([Mariano and Mariano 2012; Kynicky et al. 2012](#)). The main ore minerals in these deposits are: bastnäsite $[La,Ce,Y(CO_3)F]$, allanite $[(Ce,Ca,Y)_2(Al,Fe^{+++})_3(SiO_4)_3(OH)]$, monazite $[(Ce,La,Nd,Th)PO_4]$, apatite $[Ca_5(PO_4)_3(OH,F,Cl)]$ and pyrochlore $[(Na,Ca)_2Nb_2O_6(OH,F)]$. The placer deposits, especially sands from the shoreline formation (Ti-Zr-REE-Th), in which the REE-bearing minerals are primarily, monazite, and xenotime [YPO₄] that occur with zircon [$Zr(SiO_4)$], ilmenite [$FeTiO_3$] and from the second formation represented by cassiterite sands $[SnO_2]$ (Sn-Ta-Nb-Y) with xenotime ([Long et al. 2010; Szamałek et al. 2013](#)) are also important. In the first formation, the content of REE-bearing minerals (mainly monazite) ranges from 0.3 to 5% among heavy minerals (in India to 20%; [Paulo and Krzak 2015](#)). In turn, the share of heavy fraction can be from 3 to 60% of quartz sands that form the mainly coastal bars. Monazite and xenotime are by-products of the enrichment of ilmenite-zircons sands. The production of this type heavy minerals concentrates is carried out mainly in Western Australia, Brazil and India ([Collins and Baxter 1984; Hedrick 1997; Long et al. 2010; Paulo and Krzak 2015](#)). In turn, the production of cassiterite concentrates (along with xenotime) on the largest scales takes place on the shelf in the south-eastern Asia (e.g. in Malaysia, Thailand and Indonesia; [Economic 1988; Hedrick 1997; Szamałek et al. 2013](#)).

In Poland, the perspective of REE deposit occurrence, despite the evidence of their resources in the two deposits in the Sudety Mountains ([Kanasiewicz 1987](#)), were judged very critically by some researchers ([Paulo 1993](#)). Recognized in NE Poland by deep drilling REE mineralization associated with carbonatites and alkaline magmatism is not of any economic importance to date ([Kubicki 1987; Krzemieńska and Krzemieński 2012](#), and references therein). Marine sands from the Polish coast and bottom of the Baltic Sea were also the subjects of works in the field of the concentration of REE in heavy minerals. These studies focused around three main issues: the composition of heavy minerals and conditions of placers formation ([Zwierzycki 1947; Sawicka 1953; Łoziński and Masicka 1959; Mączka and Racinowski 1960; Wajda 1970, 1977; Kotliński 1985; Kramarska 1991](#)) prognoses of resources ([Kotliński and Kramarska 1977; Jurowska et al. 1978; Wajda 1980, 1982; Mapa geologiczna... 1989–1995; Kramarska 1993; Jones 1994; Kramarska et al. 2005](#)) and the implementation issues relating to the technology of extraction, processing and the use of components especially in marine sands from the Odra Bank, Słupsk Bank and from the Łeba region ([Akerman and Krajewski 1959; Juskowiak et al. 1976; Rosińska 1981; Łuszczkiewicz 1984; Łuszczkiewicz et al. 1988; Bagdach and Lasko 1989](#)). Oder Geological documentation of heavy minerals and sands resources in D categories were made for the Odra Bank (ca. 13 323.20 thousand tons, including 505.74 thousand tons of heavy minerals; [Kaulbarsz et al. 2013](#)).

In this article we present the pilot REE results in several samples of marine sands collected from the Polish coast of the Baltic Sea and sandbanks of the southern Baltic that were made in PIG-PIB under the theme of Mikulski et al. (2014). Other data in terms of REE distribution in other geological areas in Poland are presented in separate articles (Mikulski et al. 2015; Brański and Mikulski 2016; Oszczepalski et al. 2016).

1. Distribution and genesis of heavy minerals concentration in the Baltic marine sediments

The Pleistocene deposits of glacial and fluvioglacial accumulation that were subject to different in time processes of abrasion and re-deposition are the direct source of heavy minerals in marine sediments in the Baltic Sea (Sawicka 1953; Łoziński and Masicka 1959; Kotliński 1985). Concentrations of certain minerals in the marine sands are of secondary nature. The source rocks for these minerals are crystalline and sedimentary rocks of Scandinavia and the bottom of the Baltic Sea. The accumulation of heavy minerals is associated with the selective implementation of the movement of mineral grains of a defined size and habit, under the influence of bottom currents and a complex mechanism of grain transportation (Leontjew et al. 1982; Haas et al. 1995; Dill 2007; Dill et al. 2012). Heavy minerals from the Baltic sands are represented by transparent components (quartz, garnet, amphibole, pyroxene, epidote, chlorite, and biotite) and opaque minerals (mainly ilmenite, and rarer by magnetite). Participation of other minerals (glaucite, staurolite, tourmaline, zircon, rutile, andalusite, sillimanite and apatite) and other mineral groups (e.g. carbonates) is subordinate (Sawicka 1953; Wajda 1970; Jurowska et al. 1978). The contents of heavy minerals (tested mainly in the 0.25–0.125 mm fraction) is mostly from 1 to 2%. Concentrations above 3 weight % create an isolated field in the sands, in the shallow water of the sea within the range of the intense impact of wave and bottom currents, typically to a depth of the sea 10–30 m, and a little deeper on the thresholds separating deep-water basins (Mapa... 1989–1995; Kramarska et al. 2005).

The analysis of the distribution of concentration and granular grain composition of sediments indicates that perspective, in terms of exploration, are sediments associated with the relics of the bay-bar accumulation from the period of the Littorina Baltic Sea transgression in the Middle Holocene (Jurowska et al. 1978; Kramarska 1998). High concentrations of up to 20% occur in the sands of Odra Bank, a designated string shoals from the Eastern arm of this form to Kołobrzeg (Kramarska et al. 2005). Less well preserved relics of the spit, with the extremely high concentration of heavy minerals in the Polish zone of the Baltic Sea up to 45%, occur in Central and Eastern parts of the Słupsk Bank (Kotliński and Kramarska 1977).

On the Słupsk Bank, the total area of the three fields with the concentration of heavy minerals is a dozen km². The contents of fractions 0.063–0.25 mm in length is more than

90%. Enrichment of heavy minerals in the laminas (2–10 mm thick) are correlated with the subsurface layer of the sands at about 30 cm of the thickness ([Kotliński and Kramarska 1977](#)).

On the Odra Bank, the documentation of resources only covers two placer fields (box A and box B, a total of approximately 1,303.49 ha) in the prospective areas ([Kramarska et al. 2016](#)). The contents of heavy minerals ranges from 1.7–21.7 weight %. Placer concentrations reflect the high degree of mineralogical selection of mature granulometric deposits of shoals. Enriched sands from the Odra Bank contain, as a rule, more than 80% of the very fine and fine-grained fraction (0.063–0.25 mm) and are well or very well sorted. A layer enriched with heavy minerals, consists of lamina and streaks, a less laminae thickness of several cm, alternately enriched and poor in heavy minerals. The highest enrichment in heavy minerals is present on the bottom surface and gradually decreases with depth. The enriched layer maximum may reach up to 1 m. The average share of heavy minerals in a layer thickness of 0.5 m occurring directly from the bottom surface is about 4.5% and decreases to 2.5–4% at a depth of 0.5–1 m.

Heavy mineral resources in the sands of A and B fields have been estimated at about 505 thousand tons, including about 25 thousand tons of zirconium, almost 200 thousand tons of titanium minerals (ilmenite, rutile and leucoxene) and about 160 thousand tons of garnets ([Kaulbarsz et al. 2013; Kramarska et al. 2016](#)).

2. The methodology and scope of research

In this paper, rare earth elements were examined in 7 samples of marine sands, collected from the cores of archive boreholes drilled in the region of the Odra Bank, Słupsk Bank and in two samples from the Hel Peninsula (Fig. 1). Three tagged samples: V201, V210 and V225 come from the subsurface sections of the cores (0–0.5 m) with the same names, and represent the natural sands with heavy minerals (Fig. 2). Cores were collected with use of a vibro-corer during geological documentation works ([Kaulbarsz et al. 2013](#)).

Samples of ŁO(Zr) and ŁS(Zr) come from zirconium concentrates obtained in the processes of enrichment, separation and recovery of heavy minerals from marine sands (Bagdach and Lasko, 1989). The ŁO(Zr) sample constitutes the zirconium concentrate recovered from the sands of the Odra Bank, where sand weighing 1.2 thousand tons contained an average of 1.72% heavy minerals. While ŁS (Zr) zirconium concentrate sample was made from sands of the Słupsk Bank and primary sand sample weighing 2 thousand tons contained an average of 4.2% of heavy minerals (*ibid.*).

The samples with the symbols He1 and He2 were collected on the Hel Peninsula from a 16.6 km stretch of beach. A sample of the sands (He1; 10/13/13) was taken from the beach drift (Fig. 2a), and sample (He2; 10/13/14) from the same place but from the score in the trench with a depth of 1 m (Fig. 2b). The 2 samples mentioned above were the subject of classic panning and heavy mineral concentrates were obtained. The He1 sample of marine

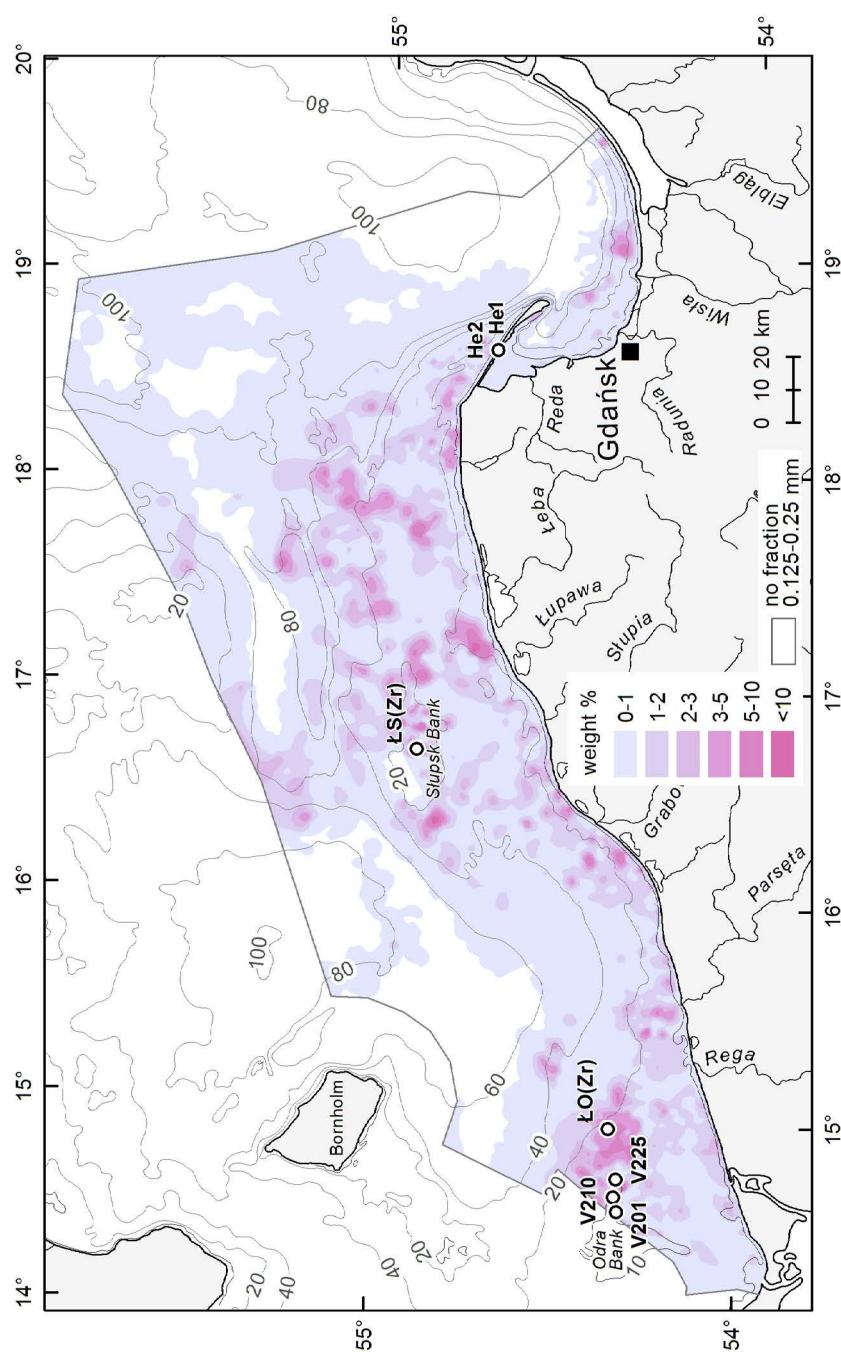


Fig. 1. The location of the samples site collected for REE analyses on the background of the map contents of heavy minerals in the surface bed of sands (fraction 0.125–0.25 mm) in the Polish marine territory (after Kramarska et al. 2005)

Rys. 1. Lokalizacja próbek pobranych do analiz REE na tle mapy zawartości mineralów ciężkich w powierzchniowej warstwie piasków (frakcja 0,125–0,25 mm) w polskich obszarach morskich (wg Kramarska i in. 2005)

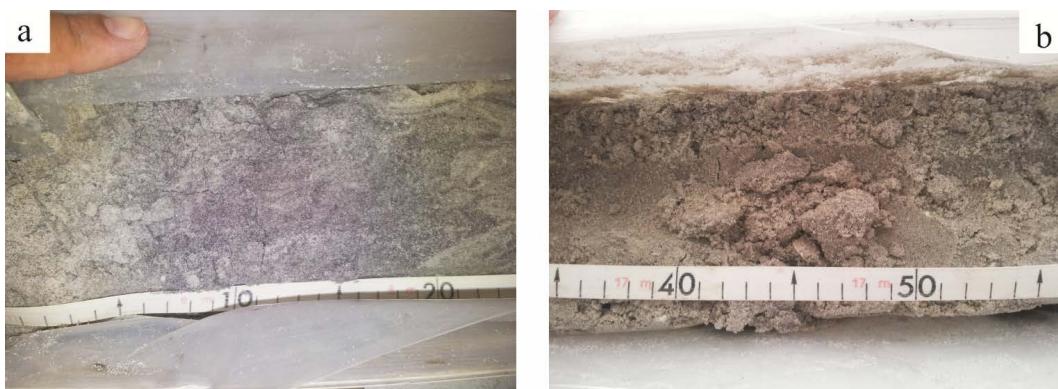


Fig. 2. Marine sands samples enriched in heavy minerals
 a) V201 borehole, depth 0–0.5 m, b) V210 borehole, depth 0–0.5 m. Odra Bank

Rys. 2. Próbki piasków morskich wzbogacone w minerały ciężkie
 a) Wiercenie V201, głęb. 0–0,5 m, b) Wiercenie V210, głęb. 0–0,5 m. Ławica Odrzana

sands contained about 30.9 % heavy minerals and He2 sample has only about 0.14 % heavy minerals. All the sand samples were subject of REE analyses.

Rare earth elements, Sc, Y, and Th analyses were performed at the Chemical Laboratory of the Polish Geological Institute – National Research Institute, using mass spectrometry with inductively coupled plasma mass spectrometry (ICP-MS technic). After acid digestion, the samples were diluted 20 times with a solution of 1% HNO_3 . The total solution of

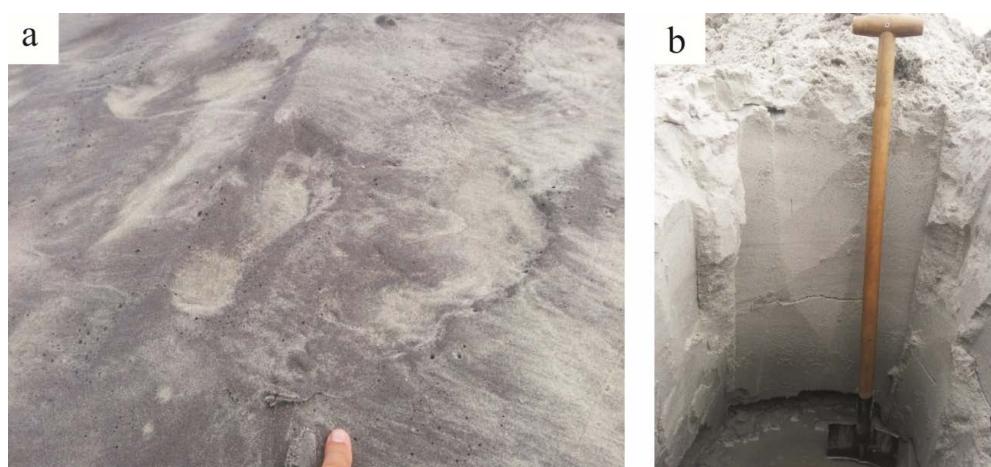


Fig. 3. a) Beach sands from the upper near shore zone enriched in heavy minerals (He1),
 b) Trench in order to collect the profile sample with a width of 5 cm and a height of ca. 1 m (He2)

Rys. 3. a) Piaski plażowe ze strefy przyboju silnie wzbogacone w minerały ciężkie (próbka He1),
 b) Wkop w celu pobrania próbki bruzdowej o szerokości 5 cm i wysokości około 1 m (próbka He2)

elements contained in the samples was achieved by the use of hydrofluoric acid and chloric acid (VII – oxidation of fluorine and chlorine in acid). Dried and powdered samples were initially treated with nitric acid (V) in order to distribute organic matter and dissolved in a mixture of perchloric and hydrofluoric acid (VII). In order to improve the procedure for dissolution, digestion was repeated three times. In the last stage, after evaporation to dryness (on a hot plate, to a temperature of $150^{\circ}\text{C} \pm 10^{\circ}\text{C}$) the residue was dissolved in dilute nitric acid (V). The solution obtained was submitted for analysis by ICP-MS. Detection limits were 0.5 ppm for LREE and 0.05 ppm for HREE.

The concentrates were made from heavy minerals samples and sections were polished for the work under the polarizing microscope (NIKON ECLIPSE LV100 POL) and electron microprobe (CAMECA SX-100). Specifications were as follows: voltage – 15 kV, current beam 10, beam focused. Acquisition times: in the peak position-20 s, the position of the background-10 s. Depositing carbon. The following spectral lines were examined: Ce – L α , La – L α , Pr – L β , Nd – L β , Sm – L β , Gd – L β and Dy – L α . The lines were selected in order to avoid interference. Analyzed on the crystals type LLIF. Standards: – synthetic glass doped with REE made by P&H Company.

3. Results of the rare earths studies in the marine sands of the Baltic Sea enriched in heavy minerals

3.1. Odra Bank

The following V201, V210 and V225 core samples represent fine-grained sands with the dominance of 0.125–0.25 mm fraction (usually $> 70\%$). The main admixture constitutes the 0.25–0.5 mm fraction, which occurs in quantities from several dozen to about 30% (Kaulbarsz et al. 2013). The heavy minerals content in samples being the subject of REE analyses belongs to the highest in the entire area of the Odra Bank covered by the resource evaluation. In the trench (profile) samples (V225 and V210) collected from the upper (0–0.5 m) part of the cores, their content are 4.64 and 6.15%, respectively. The highest contents of heavy minerals (c.a. 21.7% weight %) was found in the V201 sample. In a layer from a depth of 0.5–1 m below the seabed the heavy minerals contents falls below 3 weight %. Research of the 20-centimeter core segments shows a progressive decline in heavy minerals content with the depth.

Rare earth elements and thorium were found as a result of the carried out ICP-MS chemical analysis in the all samples (Table 1). Mainly a group of the light lanthanides with a high content of cerium, lanthanum and neodymium occurs in the marine sand samples. The content of yttrium, which in the V201 sample is dominant over the rare earths, is noteworthy. The thorium content is much lower than the listed elements. There is a clear relationship

Table 1. The content of REE, Sc, Y, and Th in marine sands as well as in the heavy minerals concentrates

[samples: LO(Zr) and LS(Zr)] from the southern Baltic bottom and of the Hel Peninsula beach

Tabela 1. Zawartość REE, Sc, Y i Th w próbkach piasków morskich jak również w koncentracie mineralów ciężkich [próbki: LO(Zr) i LS(Zr)] z dna południowego Bałtyku i plaży Półwyspu Helskiego

Sample number	Σ REE	Sc	Y	La	Ce	Pr	Nd	Sm	Eu	Gd	Tb	Dy	Ho	Er	Tm	Yb	Lu	Th
mg/kg																		
V201	156.15	23.2	69.0	24.5	51.7	6.2	24.3	5.27	0.74	5.81	1.28	10.28	2.59	9.08	1.54	11.1	1.76	11.32
V210	92.93	7.9	25.6	16.8	35.4	4.2	16.0	3.20	0.42	3.03	0.57	4.09	0.97	3.21	0.54	3.88	0.62	7.58
V225	63.03	2.5	9.7	12.9	26.3	3.0	11.3	2.14	0.26	1.74	0.28	1.72	0.37	1.20	0.19	1.41	0.22	6.09
LO(Zr)	8 786.7	14.7	332.0	1 947.1	3 921.7	465.9	1 735.0	297.09	10.86	208.52	23.33	99.10	14.21	33.5	4.07	22.8	3.55	892.16
LS(Zr)	5 117.54	15.9	276.4	1 153.8	2 324.5	267.0	960.5	154.43	6.45	107.22	13.22	67.72	10.22	26.7	3.67	23.3	3.79	473.82
He1	41.74	1.2	5.5	8.4	17.8	2	7.8	1.48	0.24	1.22	0.18	1.02	0.21	0.6	0.1	0.61	0.1	3.13
He2	1 371.16	38	134	290	600	68.4	256	46.7	1.62	34.9	4.76	26.2	5.07	15.6	2.4	17	2.6	147

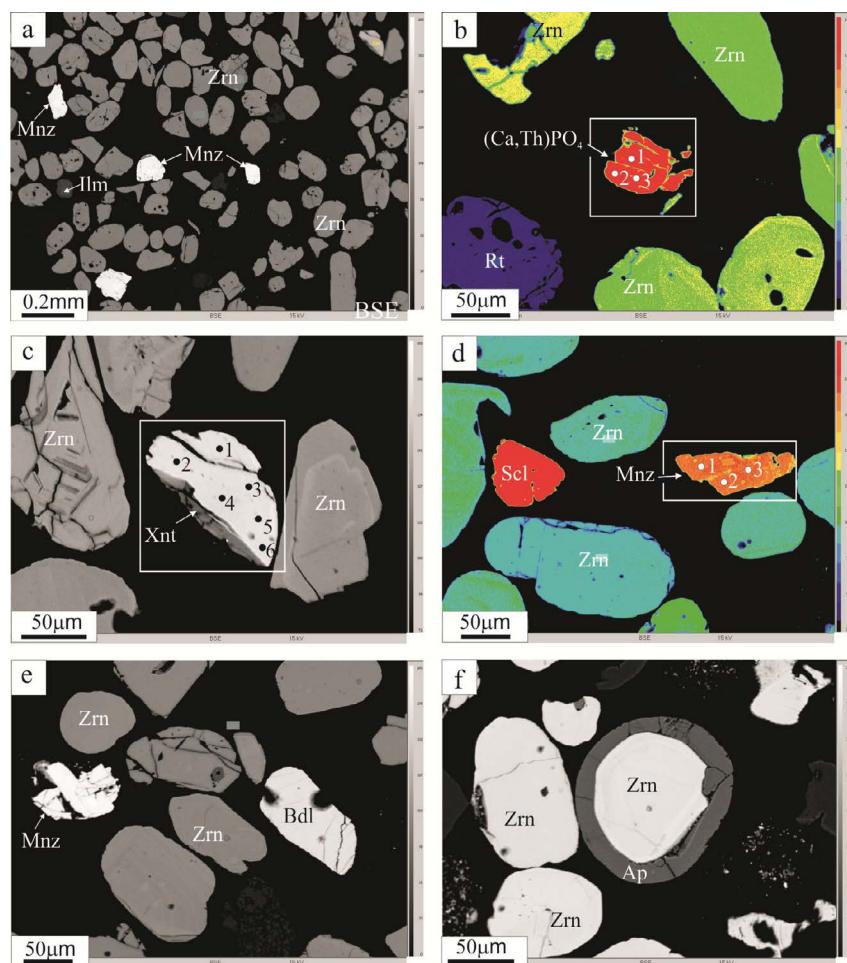


Fig. 4. The heavy minerals concentrate from the Odra Bank with visible well-rounded grains. Sample no. LO/P-4
 a) Zircon grains dominate among minerals in the concentrate (Zrn; darkgrey). Monazite grains (Mnz; white) are subordinate and ilmenite (Ilm) appears as single grains. Back-Scattered Electron Image (BSEI)/field 01/photo-1 see Table 2, b) BSEI in artificial colors reveals different minerals in heavy minerals concentrate; (Ca,Th)PO₄ – Th apatite; Rt – rutile; Zrn – zircon, c) Grains of zircon (Zrn) and xenotime (Xnt) with visible point of SEM analyses. BSEI/field 04/photo-2, d) BSEI in artificial colors reveals different minerals in heavy minerals concentrate; Scl – scheelite; Zrn – zircon; Mnz – monazite. BSEI/field 02/photo-2, e) Well-rounded zircon grains (Zrn) together with baddeleyite (Bdl) and monazite (Mnz). BSEI. Grain of zircon (Zrn) with apatite (Ap) rim. BSEI

Rys. 4. Koncentrat minerałów ciężkich z Ławicy Odrzanej z widocznym dobrym obtoczeniem ziarn. Próbka nr LO/P-4 a) Ziarna cyrkonu dominują ilościowo w koncentracie minerałów ciężkich (Zrn; ciemnoszary). Ziarna monacytu (Mnz; białe) są ilościowo podrzędne i podobnie jak ilmenit (Ilm) występują jako pojedyncze ziarna. Obraz elektronów wstecznie odbitych (BSEI) /obszar 01/foto-1 patrz tab. 2, b) Obraz elektronów wstecznie odbitych w sztucznych barwach uwypukla różnice w obecności minerałów w koncentracie; (Ca,Th)PO₄ – Th apatyt; Rt – rutyl; Zrn – cyrkon, c) Ziarna cyrkonu (Zrn) i ksenotymu (Xnt) z widocznymi punktami analiz SEM. BSEI/obszar 04/foto-2, d) BSEI w sztucznych barwach uwypukla różnice w obecności minerałów w koncentracie; Scl – scheelite; Zrn – cyrkon; Mnz – monacyt. BSEI/obszar 02/foto-2, e) Dobrze obtoczone ziarna cyrkonu (Zrn) w towarzystwie z baddeleyitem (Bdl) i monacytem (Mnz). BSEI. Ziarno cyrkonu (Zrn) z otoczką apatytu (Ap). BSEI

of the REE content with the presence of heavy minerals in sediments. The highest concentrations of rare earth elements are present in the V201 sample, which has c.a. 21.7 weight % of heavy minerals. They are most often 2–3 times higher than in V210 and V225 samples.

Zircon dominates in the heavy minerals concentrate ($\text{LO}(\text{Zr})$) and the contents of rare earth elements is many times higher (even 100 times) than in the natural marine sands. The light lanthanides also dominate in the zircon concentrate sample $\text{LO}(\text{Zr})$. The cerium concentration reaches 3.9 g/kg, and lanthanum and neodymium occur in the amount of 1.9 and 1.7 g/kg. The contents of praseodymium, yttrium, gadolinium and samarium are in the range of 0.5–0.2 g/kg. Components of the subgroups of heavy lanthanides are in the range from several to almost 100 mg/kg. In relation to the contents of the lanthanides in comparison to their content in sand samples, the content of yttrium is low (332 mg/kg) and scandium (14.7 mg/kg) was negligible. However, thorium reaches almost 0.9 g/kg of concentrate. Microscopic and microprobe research revealed a concentrate of the dominant presence of zircon in the $\text{LO}(\text{Zr})$ sample and also the appearance other heavy minerals such as garnet, topaz, rutile or apatite (in total of up to a dozen percent volume of concentrate). Zircons are well rounded and generally have sizes c.a. of 100 μm in length (range from 80 to 150 μm). They show different content for Hf and a varied admixture of yttrium. Monazites which are the main media of LREEO (55–60 weight %) and Th (c.a. 3–8 weight %; Table 2) have up to several percent in concentrate. Monazites, like zircons are well rounded and the sizes of the grains are in the range from 100 to 250 μm (Fig. 4a, 4d–e). Xenotime single well-rounded grains are up to 100 μm in diameter (Fig. 4c) and apatite grains were also found (Fig. 4b). Apatite grains are slightly smaller in size (50–70 μm in diameter) and may form very spectacular rims around the zircon core (Fig. 4f). It's a variety rich in thorium occurs among apatite (up to 47.6 weight % Th; Table 3). Xenotime has a high yttrium contents (43–44 weight % of Y_2O_3) and an admixture of HREEO (sum >15 weight %; Table 3). Rutile (without Nb-additives), and ilmenite also occur in heavy concentrations, however in subordinate quantities. Single grains of baddeleyite or scheelite (with a diameter of approx. 70 μm) were also found (Fig. 4d–e).

3.2. Słupsk Bank

The light lanthanides also dominate in the heavy minerals concentrate of the $\text{LS}(\text{Zr})$ sample from the Słupsk Bank. The cerium concentration reaches 2.3 g/kg, and lanthanum and neodymium is present in the amount of 1.1 and 0.96 g/kg, respectively (Table 1). Praseodymium, yttrium, gadolinium and samarium occur in contents from 0.1 to 0.3 g/kg. Components of the subgroups of heavy lanthanides are in the range of several (Lu, Tm) to almost 68 mg/kg (Dy). Compared with the sand samples, there is a low content of yttrium (276 mg/kg) and negligible of scandium (15.9 mg/kg) in relation to the other lanthanides. However, thorium reaches nearly 0.5 g/kg in the concentrate.

Table 2. WDS composition (in wt.%) of monazite grains in the heavy minerals concentrate from the Odra Bank (LO-P-4)
 Tabela 2. Skład chemiczny (w % wag.) monazytu z koncentratu mineralów ciężkich z Lawicy Odrzańskiej (LO-P-4) na podstawie badań na mikrosondzie elektronowej (EPMA)

	LO_P-4_area-02_phot-2			LO_P-4_area-03_phot-2			LO_P-4_area-03_phot-3			LO_P-4_area-07_phot-1			LO_P-4_area-08_phot-1			
Formula	1 / 1	2 / 1	3 / 1	1 / 1	2 / 1	3 / 1	4 / 1	1 / 1	2 / 1	3 / 1	1 / 1	2 / 1	3 / 1	1 / 1	2 / 1	3 / 1
Weight % Oxide																
S	0.004	0.004	0.011	0.016	0.013	0.006	0.007	0.008	0.023	0	0.008	0.012	0.012	0.008	0.008	0.006
K ₂ O	0.003	0	0.011	0.002	0.005	0.021	0.003	0.015	0.011	0.012	0.019	0.003	0.001	0.003	0	0.006
CaO	1.184	1.165	1.228	1.086	1.154	1.143	1.136	1.834	1.828	1.784	0.549	0.527	0.516	0.977	1.019	0.992
FeO	0.026	0.003	0.024	0	0.009	0.012	0.004	0.026	0	0.022	0	0	0	0.005	0	0.044
SrO	0.031	0.015	0	0.023	0.028	0.01	0	0.001	0	0.004	0.028	0.03	0.018	0	0.037	0.043
PbO	0.69	0.622	0.687	0.445	0.485	0.505	0.502	0.833	0.83	0.783	0.305	0.305	0.298	0.481	0.482	0.506
Al ₂ O ₃	0.006	0.012	0	0	0.025	0.019	0.031	0	0	0.014	0.026	0.024	0.028	0.024	0.002	0.007
Y ₂ O ₃	1.217	1.334	1.274	1.211	1.36	1.287	1.13	3.494	3.358	2.252	1.01	0.919	0.947	0.393	0.475	0.415
La ₂ O ₃	13.369	13.279	13.015	14.334	13.921	14.377	14.584	10.526	10.727	11.332	15.152	15.274	15.07	14.939	14.249	15.223
Ce ₂ O ₃	27.795	27.59	28.586	28.898	28.731	29.084	29.755	26.694	26.287	27.405	33.505	33.669	33.115	31.442	31.042	31.512
Pr ₂ O ₃	2.756	2.868	2.776	2.903	2.885	2.698	2.636	2.532	2.67	2.741	2.775	2.9	2.949	2.799	2.808	2.915
Nd ₂ O ₃	10.914	11.165	10.775	10.788	11.108	10.951	10.643	10.266	10.55	9.984	10.178	10.514	11.499	11.6	11.074	
Sm ₂ O ₃	1.507	1.435	1.329	1.476	1.552	1.436	1.475	1.733	1.664	1.877	1.379	1.267	1.309	1.467	1.447	1.482
Eu ₂ O ₃	0	0.019	0.004	0	0	0	0	0	0.123	0	0	0	0	0	0	0
Gd ₂ O ₃	1.129	1.298	1.234	1.319	1.312	1.27	1.086	1.749	1.616	0.743	0.77	0.717	0.775	0.989	0.92	
Dy ₂ O ₃	0.274	0.367	0.318	0.284	0.361	0.386	0.263	0.805	0.858	0.55	0.205	0.215	0.19	0.106	0.135	0.022
SiO ₂	1.109	1.078	1.185	0.529	0.516	0.497	0.471	0.392	0.417	0.475	0.55	0.547	0.574	0.521	0.574	0.565
ThO ₂	8.267	8.066	8.307	5.725	5.996	5.973	5.626	7.205	7.301	7.648	3.393	3.318	3.738	5.409	5.658	5.457
UO ₂	0.185	0.196	0.188	0.187	0.237	0.196	0.144	0.997	1.016	0.793	0.209	0.19	0.173	0.166	0.142	0.154
P ₂ O ₅	28.977	29.078	28.943	29.678	29.517	29.814	29.813	30.36	30.215	29.941	29.7	29.581	29.442	29.546	29.293	29.115
As ₂ O ₅	0	0	0	0	0	0	0	0.037	0.002	0.062	0.015	0	0.052	0	0	0
Total	99.443	99.594	99.893	98.904	99.215	99.683	99.472	99.342	99.146	99.935	99.539	99.783	99.61	100.558	99.961	100.458

Table 3. WDS compositions (in wt.%) of Th-apatite in the heavy minerals concentrate from the Odra Bank (LO-P-4-area-01-phot-1) and of xenotime grains from the Odra (LO-P-4) and Słupsk (LS-K-7) Banks

Tabela 3. Skład chemiczny (w % wag.) Th-apatytu z koncentratu mineralów ciężkich z Lawicy Odrzańskiej (LO-P-4) i Lawicy Słupskiej (LS-K-7) na podstawie badań na mikrosondzie elektronowej (EPMA)

Formula	LO_P-4_area-01_phot-1						LO_P-4_area-04_phot-2						LO_K-7_area-06_phot-1					
	1/1	2/1	3/1	Formula	1/1	2/1	3/1	4/1	5/1	6/1	1/1	2/1	3/1	4/1	1/1	2/1	3/1	4/1
	Weight % Oxide																	
S	0.025	0.066	0.01	S	0.008	0.008	0.014	0.01	0.008	0.007	0.023	0.024	0.028	0.017				
K ₂ O	0.253	0.168	0.208	K ₂ O	0.003	0.019	0.012	0.011	0.014	0.014	0	0.005	0.011	0				
CaO	11.06	10.206	9.623	CaO	0.2	0.208	0.216	0.174	0.241	0.115	0.147	0.05	0.1	0.194				
FeO	0.167	0.173	0.221	FeO	0	0.04	0.025	0	0	0	0	0	0	0.021	0			
SrO	1.695	1.616	1.508	SrO	0.01	0.006	0.059	0	0	0	0.01	0	0	0	0	0	0	
PbO	0.039	0.064	0.066	PbO	0.31	0.274	0.326	0.283	0.438	0.132	0.059	0.005	0.054	0.076				
Al ₂ O ₃	0.263	0.286	0.313	Y ₂ O ₃	43.565	43.734	44.065	44.752	43.71	43.619	38.962	40.525	39.91	38.512				
Y ₂ O ₃	1.432	1.378	1.197	Nd ₂ O ₃	0.356	0.352	0.51	0.46	0.478	0.265	0.351	0.409	0.398	0.455				
La ₂ O ₃	2.357	2.027	1.832	Sm ₂ O ₃	0.416	0.476	0.439	0.456	0.493	0.485	1.162	1.091	1.095	1.298				
Ce ₂ O ₃	2.27	2.29	1.569	Eu ₂ O ₃	0	0.073	0.068	0.064	0.041	0.037	0.696	0.545	0.514	0.761				
Pr ₂ O ₃	0.352	0.366	0.237	Gd ₂ O ₃	1.499	1.542	1.613	1.76	1.703	1.438	5.313	4.645	4.057	5.621				
Nd ₂ O ₃	1.684	1.371	1.234	Tb ₂ O ₃	0.464	0.386	0.536	0.428	0.423	0.379	1.226	1	0.864	1.162				
Sm ₂ O ₃	0.265	0.345	0.274	Dy ₂ O ₃	5.012	5.027	5.193	5.4	5.154	4.77	7.852	7.511	7.407	7.288				
Eu ₂ O ₃	0.038	0.011	0.163	Ho ₂ O ₃	1.294	1.207	1.242	1.153	1.298	1.436	1.409	1.395	1.279	1.207				
Gd ₂ O ₃	0.474	0.362	0.304	Er ₂ O ₃	4.195	4.199	3.932	4.054	3.915	4.661	3.214	3.286	3.699	2.941				
Dy ₂ O ₃	0.21	0.246	0.217	Yb ₂ O ₃	4.648	4.569	3.955	3.875	4	6.192	3.48	3.879	4.625	3.696				
SiO ₂	0.44	0.473	0.859	SiO ₂	0.258	0.282	0.316	0.223	0.384	0.157	1.4	1.882	2.335	0.809				
ThO ₂	41.546	44.995	47.595	TiO ₂	0	0	0	0.039	0	0	0.335	0.376	0.477	1.076				
UO ₂	0	0	0	ThO ₂	0.035	0.063	0.079	0.052	0.07	0.07	0.037	0	0.079	0.005				
P ₂ O ₅	29.855	29.464	28.361	UO ₂	1.075	1.026	1.228	0.81	1.389	0.431	0.369	0.392	0.471	0.303				
As ₂ O ₅	0	0.022	0.034	P ₂ O ₅	35.606	35.515	35.653	35.442	35.407	34.809	33.236	32.908	32.313	33.889				
Total	94.426	95.929	95.824	As ₂ O ₅	0.035	0	0	0	0	0	0.147	0.086	0.055	0.063				
				Total	98.99	99.008	99.447	99.165	99.017	99.426	100.014	99.791	99.374					

Table 4. WDS composition (in wt.%) of monazite grains in the heavy minerals concentrate from the Słupsk Bank (LS-K-7)

Tabela 4. Skład chemiczny (w % wag.) monacytu z koncentratu mineralów ciężkich z Lawicy Szupskiej (LS-K-7) na podstawie badań na mikrosondzie elektronowej (EPMA)

Formula	LS_K-7_area-04_phot-2			LS_K-7_area-05_phot-1			LS_K-7_area-08_phot-1			LS_K-7_area-09_phot-1		
	1 / 1	2 / 1	3 / 1	4 / 1	5 / 1	1 / 1	2 / 1	1 / 1	2 / 1	1 / 1	2 / 1	3 / 1
Weight % Oxide												
S	0.015	0.08	0.032	0.054	0.255	0.003	0.015	0.01	0.001	0.012	0.017	0.017
K ₂ O	0.003	0.01	0.001	0.024	0.003	0.008	0.006	0.035	0.045	0.027	0.005	0.01
CaO	1.324	1.26	1.252	1.461	4.288	0.384	0.355	0.855	1.382	1.025	1.089	1.063
FeO	0.083	0.084	0.1	0.533	1.328	0	0	0.024	0.032	0.025	0	0
SrO	0.037	0.008	0.015	0.041	0.113	0.028	0.037	0.079	0.016	0.014	0.008	0.049
PbO	0.755	0.586	0.46	1.235	0.071	0.344	0.359	0.037	0.106	0.523	0.546	0.513
Al ₂ O ₃	0.03	0.05	0.024	0.028	0.06	0.018	0	0.017	0.014	0.004	0.015	0.004
Y ₂ O ₃	1.056	0.832	0.79	1.795	13.454	0.779	0.782	0.595	1.937	2.57	2.498	2.483
La ₂ O ₃	11.397	11.774	12.313	9.852	4.628	15.518	15.465	14.484	13.667	12.49	12.814	12.499
Ce ₂ O ₃	26.135	28.073	28.168	22.244	10.365	32.092	32.532	30.643	28.952	28.721	28.942	29.334
Pr ₂ O ₃	2.804	2.862	3.034	2.482	0.995	2.6	2.951	2.9	2.964	2.727	2.817	2.856
Nd ₂ O ₃	11.501	12.699	12.205	9.784	3.71	11.168	11.155	11.715	10.548	10.738	10.338	10.383
Sm ₂ O ₃	2.154	2.255	2.192	1.949	0.858	1.146	1.091	2.051	1.535	1.875	1.677	1.731
Eu ₂ O ₃	0	0.082	0.039	0.119	0.418	0	0	0	0.048	0	0	0.082
Gd ₂ O ₃	1.701	1.702	1.845	1.524	2.059	0.707	0.734	1.448	1.322	1.453	1.446	1.557
Dy ₂ O ₃	0.387	0.357	0.384	0.508	2.233	0.152	0.21	0.233	0.583	0.601	0.589	0.554
SiO ₂	1.286	0.929	0.732	2.977	5.611	1.005	0.86	0.336	0.224	0.709	0.562	0.56
ThO ₂	10.247	8.157	6.958	16.744	25.071	4.769	4.245	4.97	5.754	6.033	5.783	5.711
UO ₂	0.023	0.003	0	0.545	0.012	0.055	0.038	0.049	0.385	0.32	0.368	0.356
P ₂ O ₅	28.434	28.936	29.398	24.688	18.141	28.88	29.099	30.01	30.406	29.302	29.873	29.358
As ₂ O ₅	0.023	0	0	0.034	0	0	0.023	0.078	0	0.021	0.043	0.014
Total	99.396	100.738	99.944	98.621	93.673	99.657	99.96	100.568	99.921	99.25	99.428	99.135

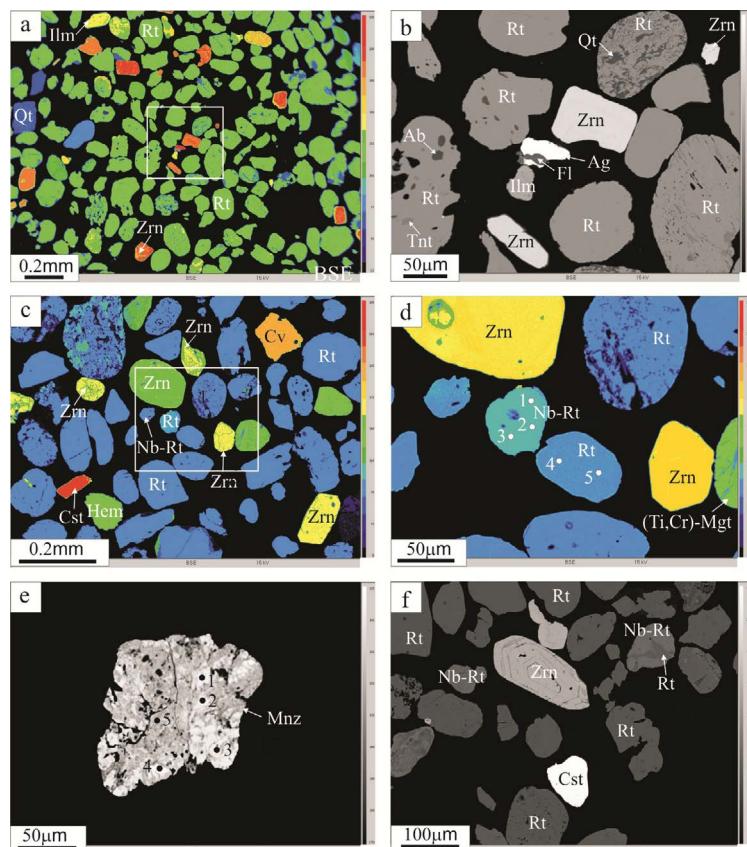


Fig. 5. The heavy minerals concentrate from the Słupsk Bank with visible well-rounded grains. Sample no. LS-K-7
 a) Rutile (Rt; green) grains dominate among minerals in the heavy minerals concentrate; Zrn – zircon (orange); Ilm – ilmenite; Qt – quartz (blue). BSEI. Fragment in square enlarge on the next photo, b) Grains of rounded rutile, together with zircon (Zrn) and ilmenite (Ilm) and with single grain of native silver intercalated with fluorite (Fl). Ab – albite; Tnt – titanite; BSEI, c) BSEI in artificial colors reveals different minerals in heavy minerals concentrate; Nb-Rt – Nb rutile; Rt – rutile; Zrn – zircon; Hem – hematite; Cst – cassiterite; Cv – covellite. Fragment in square enlarge on the next photo, d) BSEI in artificial colors with visible point of SEM analyses. Zrn – zircon; Rt – rutile; (Ti, Cr)-Mgt – (Ti, Cr) – magnetite. BSEI/field 03/photo-2, e) Rounded and fractured grain of monazite (Mnz) with visible point of SEM analyses. BSEI/field 04/photo-2, e) Rounded grains of rutile (Rt), zircon (Zrn) and cassiterite (Cst). In some rutile grains are visible darker parts enriched in niobium (Nb-Rt). BSEI

Rys. 5. Koncentrat minerałów ciężkich z Ławicy Słupskiej z widocznym dobrym obtoczeniem ziarn. Próbka nr LS-K-7. a) Ziarna rytulu (Rt; zielony) dominują wśród minerałów koncentratu; Zrn – cyrkon (pomarańczowy); Ilm – ilmenit; Qt – kwarc (niebieski). BSEI. Fragment w prostokącie jest powiększony na następnym zdjęciu, b) Obtoczone ziarna rytulu wraz z cyrkonem (Zrn) i ilmenitem (Ilm) oraz z pojedynczym ziarenkiem srebra rodzimego w przerośnięciu z fluorytem (Fl). Ab – albit; Tnt – tytanit; BSEI, c) BSEI – Obraz elektronów wstecznie odbitych w sztucznych barwach uwydruknia różnice w obecności minerałów w koncentracji; Nb-Rt – Nb rutyl; Rt – rutyl; Zrn – cyrkon; Hem – hematyt; Cst – kasyteryt; Cv – kowelin. Fragment w prostokącie jest powiększony na następnym zdjęciu, d) BSEI w sztucznych barwach z widocznymi punktami analiz SEM. Zrn - cyrkon; Rt - rutyl; (Ti, Cr)-Mgt - (Ti, Cr) - magnetyt. BSEI/obszar 03/foto-2, e) Zaokrąglone i spękane ziarno monacytu (Mnz) z widocznymi punktami analiz SEM. BSEI/obszar 04/foto-2, e) Zaokrąglone ziarna rytulu (Rt), cyrkonu (Zrn) i kasyterytu (Cst). W niektórych ziarnach rytulu widoczne są ciemniejsze strefy wskazujące na domieszkę niobiu (Nb-Rt). BSEI

Table 5. WDS composition (in wt.%) of rutile, Nb-rutile and pirochlor grains in the heavy minerals concentrate from the Słupsk Bank (LS-K-7)

Tabela 5. Skład chemiczny (w % wag.) rutylu, Nb-rutylu i pirochloru z koncentratu mineralów ciężkich z Ławicy Słupskiej (LS-K-7) na podstawie badań na mikrosondzie elektronowej (EPMA)

Formula	LS_K-7_area-03_photo-2					LS_K-7_area-07_photo-2			
	1/1	2/1	3/1	4/1	5/1	1/1	2/1	3/1	4/1
Weight % Oxide									
F	0	0	0	0.004	0	2.663	2.66	2.655	2.681
S	0.002	0.021	0.004	0	0.002	0.052	0.053	0.05	0.06
Cl	0.014	0	0.001	0.005	0.005	0	0	0.023	0.013
Na ₂ O	0	0	0	0	0	3.627	3.674	3.652	3.771
K ₂ O	0.01	0	0.013	0.007	0.01	0.013	0.011	0.012	0.002
MgO	0	0	0	0	0	0.147	0.148	0.144	0.269
CaO	0.008	0.005	0	0.003	0.011	17.122	17.121	17.131	17.109
MnO	0.034	0.012	0	0	0	0.175	0.171	0.181	0.167
FeO	3.29	3.192	3.352	0.635	0.647	2.111	2.056	1.983	2.008
SrO	0	0.014	0	0.018	0.018	0.295	0.261	0.24	0.233
PbO	0.013	0.009	0	0.019	0.004				
Al ₂ O ₃	0.018	0.036	0.038	0.099	0.077	0.118	0.119	0.137	0.147
Y ₂ O ₃	0	0.004	0.015	0	0	0.294	0.273	0.264	0.29
La ₂ O ₃	0.053	0	0.03	0	0	0.98	0.791	0.852	0.761
Ce ₂ O ₃	0.201	0.172	0.179	0.156	0.196	4.712	4.797	4.565	4.467
Pr ₂ O ₃	0	0.05	0	0	0.048	0.278	0.372	0.156	0.521
Nd ₂ O ₃	0	0	0	0	0	1.003	1.106	1.079	1.105
Sm ₂ O ₃	0	0	0	0	0.024	0.157	0.183	0.186	0.066
SiO ₂	0.025	0.004	0.013	0.014	0.041	0.031	0.017	0.021	0.022
TiO ₂	89.533	90.484	89.592	97.615	97.57	0.241	0.224	0.174	0.194
ThO ₂	0	0	0	0	0.01	0.039	0.056	0.045	0.052
UO ₂	0.005	0	0	0.001	0.023	0	0	0.005	0
P ₂ O ₅	0.008	0.012	0.016	0	0	0.051	0.008	0	0.025
Nb ₂ O ₅	5.662	5.418	5.773	0.917	0.912	63.224	63.838	63.638	63.429
Ta ₂ O ₅	0.351	0.133	0.408	0.056	0.04	0	0.048	0.102	0.259
Total	99.226	99.565	99.434	99.548	99.64	97.335	97.987	97.295	97.65

Microscope and microprobe studies showed the domination of rutile in the LS(Zr) heavy minerals concentrate sample. Rutiles constitute almost 65–70% of all grains (Fig. 5a). Rutiles have sizes ranging from 50 to 150 µm in diameter, rounded edges and they are commonly intercalated with quartz and ilmenite or less frequently with xenotime or zircon. The rutile variety also appears with a high admixture of niobium (5–6 weight % of Nb₂O₅; Table 5). Nb-bearing rutile's are generally a bit smaller (approx. 50 µm in diameter) in relation to common rutile grains (Fig. 5c–5d, 5f). Albite or titanite inclusions have been found within the larger grains of rutile (about 100 µm in diameter) (Fig. 5B). The zircon grains are the second component (a dozen percent share) in the heavy minerals concentrate. Zircons generally have sizes ranging from 70 to 130 µm in diameter. Single grains of copper minerals (covellite and cuprite), cassiterite (Fig. 5c, 5f) as well as native silver intercalated with fluorite appear in the concentrate (Fig. 5a, 5b). Monazite found in concentrate revealed an usually high concentration of LREO (sum >50 weight %, Table 4) and moderate ThO₂ admixtures (7–10 weight %). On the other hand, thorium and yttrium enrichments (maximum contents of ThO₂ and Y₂O₅ ~25 and 13.4 weight %, respectively) are poorer in LREEO (sum 30–40 weight %) monazite.

In the heavy minerals concentrate well-rounded grains of magnetite (80–200 µm in diameter), ilmenite and single grains of xenotime (of sizes 70–110 µm in diameter) are present also as well as strongly altered grains of monazite (up to 150 µm in diameter; Fig. 5e; Table 4). Monazite was also found in the form of inserts in zircon grains. Xenotime has

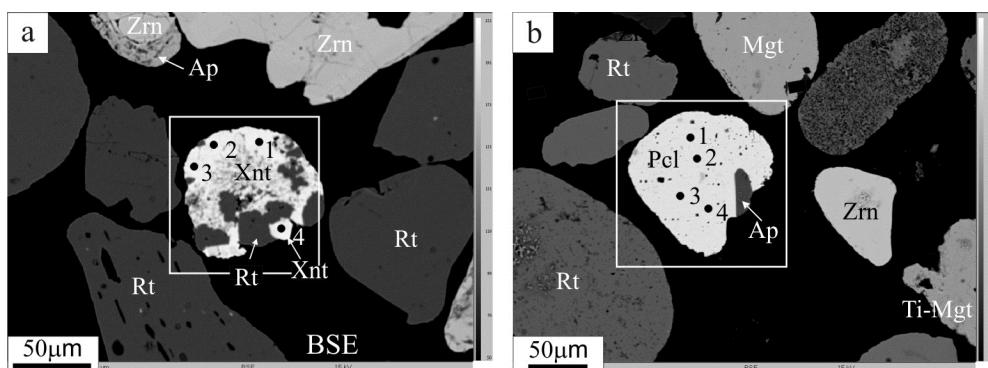


Fig. 6. The heavy minerals concentrate from the Słupsk Bank with visible well-rounded grains of different minerals. Sample no. LS-K-7

a) Well-rounded grain of xenotime (Xnt; with visible point of SEM analyses) intercalated with rutile (Rt).

The one of the zircon (Zrn) grain with apatite (Ap) rim is visible. BSEI/field 06/photo-1, b)

Grains of rounded pyrochlore (Pcl) with insert of apatite (Ap). Ti-Mgt – Ti-magnetite; BSEI/field 07/photo-2

Rys. 6. Koncentrat minerałów ciężkich z Ławicy Słupskiej

z widocznym dobrym obtoczeniem różnych minerałów. Próbka nr LS-K-7

a) Dobrze obtoczone ziarno ksenotytu (Xnt; z widocznymi punktami analiz SEM) przerastające się z rutylem (Rt). Widoczne jest jedno z ziarn cyrkonu (Zrn) z otoczką apatytu (Ap). BSEI/obszar 06/foto-1,

b) Zaokrąglone ziarna pirochloru (Pcl) z wrostkami apatytu (Ap). Ti-Mgt – Ti-magnetyt;

BSEI/obszar 07/foto-2

a high contents of yttrium (Y_2O_3 , 38–40.5 weight %) and HREEO (sum >25 weight %; Table 3). Xenotime may form intercalation with rutile (Fig. 6A). In addition, a strongly rounded single grain of pirochlor (with a diameter of approx. 100 μm) and a high content of Nb (Nb_2O_5 63–64 weight %; Table 5), and low admixture of Ce and La (c.a. 6–7 weight % of LREEO) with the apatite inserts were identified (Fig. 6b).

3.3. Hel Peninsula

As a result of the ICP-MS chemical analysis, the presence of rare earths represented mainly by the lanthanides and another elements such as thorium, yttrium and scandium was found in one of the samples (Table 1). In the shore sands sample (# He2) from the trench (Fig. 3B) the significant enrichment in the light lanthanides group with a high proportion of cerium, and then lanthanum and neodymium is characteristic. The concentration of yttrium is also noteworthy. Besides, part of the thorium is also high in this sample (147.4 ppm). The sum of REE in the first sample (#He1) from this area is very low (40 ppm). In turn, the sum of REE is much higher in the second sample – 0.14 weight %. In this sample, the light lanthanides also dominate. The cerium concentration reaches c.a. 0.6 g/kg, and lanthanum and neodymium concentration exists in the amount of 0.3 and 0.26 g/kg, respectively. The content of neodymium and yttrium is in the range of 100–250 mg/kg. Components of the heavy lanthanides subgroups are in the range from several to twenty some mg/kg (for example Dy). In comparison with a beach sands sample, (He1) collected from the surface has a significantly increased concentration of REE (>40-times). And if we compared this sample to the other 3 Baltic marine sand samples from the Odra Bank (Table 1), we can notice that He2 sample enrichment in REE is from 5 to 15 times greater. The exceptions are ŁO(Zr) and ŁS(Zr) samples of heavy minerals concentrates which contain total sum of rare earths from 4 to 6 times higher than in the He2 sample. The comparison of REE content in samples to chondrite (Fig. 7) points to their considerable enrichment in LREE (3 samples are enriched more than 1000 times) and much lower in HREE (at the level of about 100-times). In all the samples examined by ICP-MS, the total sum of REE ranges from traces (40 ppm) to 0.9% (Table 1).

The distribution of rare earth elements content in the all samples tested by ICP-MS method indicate a predominance of light lanthanides, including cerium, which remains in close correlation with the presence of grains of monazites. Monazites have been found up to a few percent of total volume of heavy minerals concentrate. The chemical composition of monazites revealed during microprobe analyses indicates a high contents of Ce_2O_3 (max. 32.5 weight %), and of Nd_2O_3 (11–13 weight %) and moderate contents of La_2O_3 (max. 15.5 weight %). In turn, relatively high yttrium content in the heavy minerals concentrate is due to the presence of xenotime. Increased contents of neodymium (0.017%) and thorium (0.0008%) were also found in this sample. The neodymium content is strongly correlated with the presence of pirochlor and Nb-bearing rutile in concentrate grains. On the other

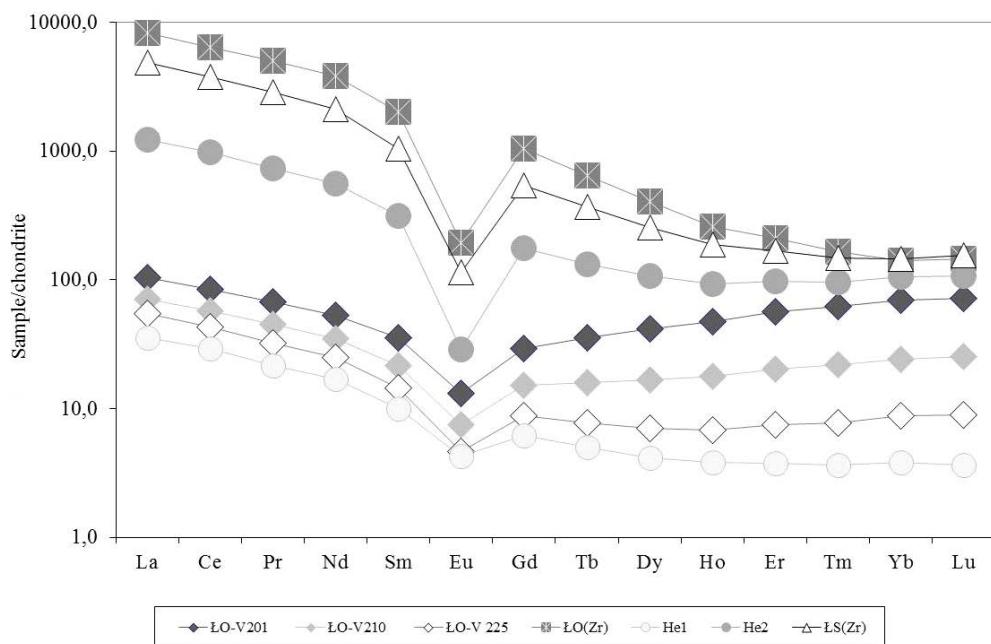


Fig. 7. The characteristics of the rare earths in the samples of marine sands and zircon concentrates [samples # LO(Zr) and LS(Zr)] from the Baltic Sea area normalized to chondrite (after McDonough and Sun 1995)

Rys. 7. Znormalizowany wykres logarytmiczny koncentracji REE w próbkach piasków i koncentratów cyrkonu [próbki nr: LO(Zr) i LS(Zr)] z regionu Morza Bałtyckiego w stosunku do zawartości w chondrycie (wg McDonough i Sun 1995)

hand, the enrichments in thorium are strongly correlated with the appearance of Th-bearing apatite and monazite in concentrate grains.

Summary

The rare earth elements results of pilot analytical work (ICP-MS methodology) in the marine sands of the Baltic Sea presented in the article have shown that some heavy minerals concentrate samples from the Odra and Słupsk Banks as well as in the one sample from the Hel Peninsula (16.6 km stretch of beach) are reaching a concentration that may be of interest in terms of economy. The results of this investigation confirmed the dependence of the REE concentration with the percentage of heavy minerals content in the marine sands. In the examined samples, it is the vast preponderance of LREE among the rare earths. The highest concentration mainly is achieved by cerium and almost two times lower by lanthanum. The total REE content in the considered 3 richest samples is from c.a. 0.14% (He2 sample from Hel Peninsula) to 0.9% (LO/Zr; heavy minerals (zircon) concentrate from the Odra Bank).

Microprobe investigations indicate that monazite is the main carrier of LREE in marine sands, and a high yttrium contents is correlated with the appearance of xenotime among the heavy minerals. Moreover, pirochlor and Nb-bearing rutile are responsible for a high neodymium concentration. Thorium is considered as strongly correlated with the appearance of Th-bearing apatite and monazite in concentrate grains. The enrichments in REE concentration is accompanied by the high contents of Th (150–900 ppm).

The previous recognition of heavy mineral resources in the Baltic sands is limited to a small area on the Odra and Słupsk Banks. More research should be done in the prospective areas situated to the North-East from the already documented placer fields with estimated resources on the Odra Bank. Furthermore, new work should be carried out in the tentatively identified areas on the Słupsk Bank, as well as along the underwater slope (paleo-slope) and on the beaches of the Hel Peninsula. Research on the minerals identification of rare earths and on the technology of recovery of REE-bearing minerals from heavy minerals concentrates should be carried out in parallel with the documentary work. This source of LREE from the heavy mineral concentrates received from the Baltic sandbanks may be interesting for recovery by the domestic economy. The presence of LREE, especially cerium, in heavy minerals concentrate is valuable due to its use in the production of catalytic converters or metal alloys. In addition, lanthanum, which is used in vehicles with hybrid drive (batteries), x-ray film or catalyst in the process of refining crude oil is present in the concentrate. In turn, neodymium is consumed during the production of strong neodymium magnets as well as for the fabrication of lasers.

This work was supported by the internal PGI-NRI research grant project no. 61.6705.1301.00.0 (Mikulski et al. 2014). The publication of this paper was financed by National Fund for Environmental Protection and Water Management, Project no. 22.9510.1601.02.1 – titled “Polish Geological Survey information activities in the area of access to data on the occurrence and availability of mineral resources that are of key importance to the national economy and energy security of Poland”. I. Wysocka are acknowledge for chemical analysis.

REFERENCES

- Akerman, K. and Krajewski, J. 1959. Studia nad selektywnym wzbogacaniem bałtyckich piasków cyrkononośnych. cz. II. *Przem. Chem.* Vol. 38 (in Polish).
- Bagdach, Z. and Lasko, S. 1989. Technologia pozyskiwania ilmenitu, rutyłu, cyrkonu i granatów z piasków morskich Ławicy Słupskiej i Odrzanej. *Technika i gospodarka morska* 7 (452), pp. 330–332 (in Polish).
- Brański, P. and Mikulski, S.Z. 2016. Rare earth elements distribution in fine-grained deposits from the uppermost Triassic and Lower Jurassic of the Polish Basin: provenance and weathering of source area (preliminary results). *Geological Quarterly* Vol. 60(2). pp. 441–450.
- Chakhmouradian, A.R. and Wall, F. 2012. Rare Earth Elements: Minerals. Mines. Magnets (and More). *Elements* Vol. 8 (5), pp. 333–340.
- Collins, L.B. and Baxter, J.L. 1984. Heavy mineral-bearing strandline deposits associated with high-energy beach environments, southern Perth Basin, Western Australia. *Australian Journal of Earth Sciences: An International Geoscience Journal of the Geological Society of Australia* Vol. 31 (3), pp. 287–292.

- Dill, H.G. 2007. Grain morphology of heavy minerals from marine and continental placer deposits, with special reference to Fe-Ti oxides. *Sedimentary Geology* Vol. 198, pp. 1–27.
- Dill et al. 2012 – Dill, H.G., Weber, B. and Klosa, D. 2012. Morphology and mineral chemistry of monazite-zircon-bearing stream sediments of continental placer deposits (SE Germany): Ore guide and provenance marker. *Journal of Geochemical Exploration* Vol. 112, pp. 322–346.
- Economic, 1988. Economic and Social Commission for Asia and the Pacific and Australian Bureau of Mineral Resources, Geology and Geophysics, 1988, Mineral sands in Asia and the Pacific: New York, United Nations, Mineral Concentrations and Hydrocarbon Accumulations in the ESCAP Region, Vol. 4, p. 129.
- EU Resolution, 2011. An effective raw materials strategy for Europe. European Parliament resolution of 13 September 2011. [Online] Available at: <http://eur-lex.europa.eu/LexUriServ/LexUriServ:2013:051E:0021:0037:EN:PDF> [Accessed: 9.10.2016].
- Galos et al. 2012 – Galos, K., Nieć, M., Radwanek-Bąk, B., Smakowski, T. and Szamałek, K. 2012. Bezpieczeństwo surowcowe Polski w Unii Europejskiej i na Świecie. *Buletyn Państwowej Inst. Geol.* Vol. 452, pp. 43–52 (in Polish).
- Galos, K. and Smakowski, T. 2008. Nowa polityka surowcowa Unii Europejskiej w obszarze surowców nie-energetycznych. *Gospodarka Surowcami Mineralnymi – Mineral Resources Management* Vol. 24(4). pp. 75–90 (in Polish).
- Haas et al. 1995 – Haas, J.R., Shock, E.L. and Sassani, D.C. 1995. Rare earth elements in hydrothermal systems: Estimates of standard partial molar thermodynamic properties of aqueous complexes of the rare earth elements at high pressures and temperatures. *Geochimica et Cosmochimica Acta* Vol. 59, pp. 4329–4350.
- Haque et al. 2014 – Haque, N., Hughes, A., Lim, S. and Vernon, C. 2014. Rare Earth Elements: overview of mining, mineralogy, uses, sustainability, and environmental impact. *Resources 2014* Vol. 3, pp. 614–635.
- Hatch, G.P. 2012. Dynamics in the global market for rare earths. *Elements* Vol. 8, pp. 341–346.
- Hedrick J.B. 1997. Rare-earths. *Mineral Industry Surveys. Annual review 1996*. USGS Reston.
- Jones, Ph. 1994. Baltic mineral sands Project. Inferred mineral resource estimate. [App. to:] Kramarska R. 1993. Poszukiwanie i rozpoznanie złóż minerałów ciężkich w rejonie Ławicy Odrzanej. Opracowanie i ocena wyników fazy I i 2. NAG PIG-PIB OGM Gdańsk. Nr arch. 338.
- Jurowska et al. 1978 – Jurowska, Z., Masłowska, M., Michałowska, M. and Trokowicz, D. 1978. *Mapa osadów dennych Ławicy Odrzanej w skali 1:200 000 z uwzględnieniem koncentracji minerałów ciężkich*. CAG PIG-OGM Gdańsk. Nr arch. 47 (in Polish).
- Juskowiak et al. 1976 – Juskowiak, O., Gustkowicz, S. and Sokołowska, G. 1976. *Badania technologiczne frakcji piaskowatej morskich osadów Bałtyku Południowego*. NAG PIG-PIB. Warszawa. nr inw. 21 172 (in Polish).
- Kanasiewicz J. 1987. Pierwiastki ziem rzadkich. Dolny Śląsk [W:] *Budowa geologiczna Polski. Złoża surowców mineralnych*. T. VI (red. R. Osika), pp. 369–371. Warszawa: Wyd. Geol.
- Kaulbarsz et al. 2013 – Kaulbarsz, D., Jurys, L., Kramarska, R. and Przedziecki, P. 2013. *Dokumentacja geologiczna złoża piasków z minerałami ciężkimi Lawica Odrzana pola A i B w kat. D*. NAG PIG-PIB. OGM Gdańsk, nr arch. 1110 (in Polish).
- Klupa, A. 2012. Cenniejsze niż złoto? Metale ziem rzadkich w światowej strategii gospodarczej. *Przegląd Strategiczny* 1, pp. 239–251 (in Polish).
- Kotliński, R. 1985. Osady dna Ławicy Ślupskiej. *Buletyn Instytutu Geologicznego* Vol. 352, pp. 5–56 (in Polish).
- Kotliński, R. and Kramarska, R. 1977. *Badania nad wytypowaniem najbardziej perspektywicznego rejonu dla poszukiwań złóż rozsypiskowych minerałów ciężkich w strefie szelfu południowego Bałtyku*. NAG PIG. OGM Gdańsk. Nr arch. 49 (in Polish).
- Kramarska, R. 1991. *Badania mineralogiczne i analiza porównawcza składników użytecznych wybranych rejonów Ławicy Odrzanej*. NAG PIG OGM Gdańsk, Nr arch. 225 (in Polish).
- Kramarska, R. 1993. *Poszukiwanie i rozpoznanie złóż minerałów ciężkich w rejonie Ławicy Odrzanej. Opracowanie i ocena wyników fazy I i 2*. NAG PIG-PIB Oddział Geologii Morza w Gdańsku. Nr arch. 338 (in Polish).
- Kramarska, R. 1998. Origin and development of the Odra Bank in the light of the geologic structure and radiocarbon dating. *Geological Quarterly* Vol. 42 (3), pp. 277–288.
- Kramarska et al. 2005 – Kramarska, R., Jegliński, W., Jurys, L., Przedziecki, P., Uścinowicz, Sz. and Zachowicz, J. 2005. *Atlas parametrów litologicznych osadów powierzchniowych południowego Bałtyku ze szczególnym uwzględnieniem geologiczno-górnictwowych warunków występowania surowców okruchowych*. NAG PIG-PIB. OGM Gdańsk. Nr arch. 753 (in Polish).

- Kramarska et al. 2016 – Kramarska R., Jegliński W., Kaulbarsz D., Pączek U., Przedziecki P., Bojakowska I., Koszka-Maroń D., Relisko-Rybak J., Uścinowicz Sz. 2016. Czwartorzęd Zatoki Pomorskiej i perspektywy surowcowe. *Przegląd Geologiczny* Vol. 64(8), pp. 552–563 (in Polish).
- Krzemińska, E. and Krzemieński, L. 2012. Alkaliczna intruzja syenitowa Mawy a perspektywy występowania pierwiastków ziem rzadkich. *Buletyn Państwowego Instytutu Geologicznego* Vol. 448, pp. 401–08 (in Polish).
- Kubicki, S. 1987. Pierwiastki ziem rzadkich. [W:] *Budowa geologiczna Polski. Złoża surowców mineralnych.* Tom VI (red. R. Osika), pp. 371–372. Warszawa: Wyd. Geologiczne (in Polish).
- Kynicky et al. 2012 – Kynicky, J., Smith, M.P. and Xu, C. 2012. Diversity of Rare Earth Deposits: The Key Example of China. *Elements* Vol. 8, pp. 361–367.
- Leontjew et al. 1982 – Leontjew, O.K., Nikiforow, L.G., Sajanow, G.A. 1982. *Geomorfologia brzegów morskich.* Warszawa: Wyd. Geologiczne (in Polish).
- Long et al. 2010 – Long K.R., Van Gosen, B.S., Foley, N.K. and Cordier D. 2010. The Principal Rare Earth Elements Deposits of the United States – A Summary of Domestic Deposits and a Global Perspective. *US Geological Survey Scientific Investigations Report 2010-5220.*
- Łoziński, J. and Masicka, H. 1959. Badania mineralów ciężkich w piaskach plażowych Zatoki Gdańskiej. *Rocznik Pol. Tow. Geol.* Vol. 32, pp. 579–599 (in Polish).
- Łuszczkiewicz, A. 1984. Technologiczna ocena możliwości wzbogacania piasków morskich Bałtyku. *Pr. Nauk. Inst. Chemii Nieorg. i Metalurgii Pierw. Rzadkich Polit. Wrocław.*, Vol. 51. Seria: Konferencje Vol. 10, pp. 107–116 (in Polish).
- Łuszczkiewicz et al. 1988 – Łuszczkiewicz, A., Kurzyca, M., Steinhoff, J. and Świerkot-Kopała, A. 1988. Ocena możliwości pozyskiwania mineralów ciężkich z piasków Ławic Ślupskiej i Odrzanej. *Przegląd Górnictwy* Vol. 10, pp. 12–17 (in Polish).
- Mączka, L. and Racinowski, R. 1960. Formy występowania skupień mineralów ciężkich na plażach Pomorza Zachodniego. *Kwartalnik Geologiczny* Vol. 13, pp. 221–232 (in Polish).
- Mapa Geologiczna dna Bałtyku w skali 1:200 000. 1989–1995. (red. J.E. Mojski). Warszawa: Państw. Inst. Geol.
- Mariano, A.N. and Mariano, A. 2012. Rare earth mining and exploration in North America. *Elements* Vol. 8, pp. 369–376.
- McDonough, W.F. and Sun, S.S. 1995. Composition of the Earth. *Chemical Geology* Vol. 120, pp. 223–253.
- Mikulski et al. 2014 – Mikulski, S.Z., Oszczepalski, S., Brański, P., Kozdrój, W., Markowiak, M., Kramarska, R., Chmielewski, A., Sadłowska, K. and Damrat, M. 2014. Weryfikacja stanu wiedzy o mineralizacji metalami ziem rzadkich (REE) wraz z pilotażową oceną ich perspektyw złożowych w Polsce z wyłączeniem obszaru kratonu wschodnioeuropejskiego. 1463/2016 NAG Warszawa (in Polish).
- Mikulski et al. 2015 – Mikulski, S.Z., Markowiak, M., Sadłowska, K., Chmielewski, A., Zieliński, G. 2015. Pilotażowe badanie pierwiastków ziem rzadkich w strefie kontaktu bloku małopolskiego z blokiem górnouśląskim. *Buletyn Państwowego Instytutu Geologicznego* Vol. 465, pp. 77–98 (in Polish).
- Moss et al. 2011 – Moss, R.L., Tzimas, E., Kara, H., Willis, P. and Kooroshy J. 2011. *Critical Metals in Strategic Energy Technologies Appendices, Assessing Rare Metals as supply-chain bottlenecks in Low-Carbon Energy Technologies:* JRC European Commission, pp. 1–159.
- Opinion 2006. Opinion of the European Economic and Social Committee on Risks and problems associated with the supply of raw materials to European industry. *Official Journal* 2006/C 309/16.
- Oszczepalski et al. 2016 – Oszczepalski, S., Chmielewski, A. and Mikulski, S.Z. 2016. Controls on the distribution of rare earth elements in the Kupferschiefer series of SW Poland. *Geological Quarterly* Vol. 60 (4). DOI: <http://dx.doi.org/10.7306/gq.1325>.
- Paulo, A. 1993. Dlaczego nie należy poszukiwać złóż rud niobu i pierwiastków ziem rzadkich w Polsce? *Pol. Tow. Mineral. Pr. Specjal.* Vol. 3, pp. 55–77 (in Polish).
- Paulo, A. 1999. Pierwiastki ziem rzadkich pod koniec XX wieku. *Przegląd Geologiczny* Vol. 47(1), pp. 34–41 (in Polish).
- Paulo, A. and Krzak, M. 2015. *Pierwiastki ziem rzadkich. Metale rzadkie.* Kraków: Wyd. AGH (in Polish).
- Radwanek-Bąk, B. 2011. Zasoby kopalni Polski w aspekcie oceny surowców krytycznych Unii Europejskiej. *Gospodarka Surowcami Mineralnymi – Mineral Resources Management* Vol. 27, pp. 5–19 (in Polish).
- Rosińska, M. 1981. *Badania technologiczne złóż rozsypliskowych różnych surowców w akwenie Bałtyku (próby odzysku cyrkonu i ziem rzadkich).* NAG PIG-PIB Warszawa (in Polish).

- Sawicka, E. 1953. Minerały ciężkie w piaskach plażowych polskiego wybrzeża Bałtyku. *Bulletin Instytutu Geologicznego*, pp. 29–35 (in Polish).
- Smakowski, T. 2011. Surowce mineralne – krytyczne czy deficytowe dla gospodarki UE i Polski. *Zeszyty Naukowe Instytutu Gospodarki Surowcami Mineralnymi i Energią PAN* Vol. 81, pp. 59–68 (in Polish).
- Smakowski et al. 2012 – Smakowski, T., Ney, R. and Galos, K., red. *Minerals Yearbook of Poland 2012*. Mineral and Energy Economy Research Institute of the Polish Academy of Sciences 2013, 559 pp.
- Szamałek, K. 2011. Rational mineral deposit management in the light of mineral resources theory. *Gospodarka Surowcami Mineralnymi – Mineral Resources Management* Vol. 27, pp. 5–15.
- Szamałek et al. 2013 – Szamałek, K., Konopka, G., Zglinicki, K. and Marciniak-Maliszewska, B. 2013. New potential source of rare earth elements. *Gospodarka Surowcami Mineralnymi – Mineral Resources Management* Vol. 29(3), pp. 59–76.
- [Online] Available at: http://minerals.usgs.gov/minerals/pubs/commodity/rare_earths/mcs-2016-raree.pdf [Accessed: 3.9.2016]
- Wajda, W. 1970. Minerały ciężkie piasków dennych polskiego wybrzeża Bałtyku. *Rocznik Polskiego Towarzystwa Geologicznego* Vol. 40 (1), pp. 131–149 (in Polish).
- Wajda, W. 1977. Badania litologiczne i mineralogiczne osadów dennych rejonu Ławicy Odrzanej. *Stud. i Mater. Ocean* Vol. 19, pp. 265–270 (in Polish).
- Wajda, W. 1980. Osady piaskiste południowego Bałtyku w aspekcie badań przydatnych gospodarczo koncentracji minerałów ciężkich. *Peribalticum I*. GTN, Gdańsk, pp. 59–78 (in Polish).
- Wajda, W. 1982. Banka Odry po rezultatach nowych geologicznych issledowani. *Peribalticum II*. GTN, Gdańsk. pp. 171–183 (in Polish).
- Zwierzycki, J. 1947. *Złoża cyrkonu na Pomorzu Zachodnim*. Hutnik (in Polish).

PILOTAŻOWE BADANIA PIERWIASKÓW ZIEM RZADKICH W PIASKACH MORSKICH BAŁTYKU WZBOGACONYCH W MINERAŁY CIĘŻKIE

Słowa kluczowe

pierwiastki ziem rzadkich, minerały ciężkie, piaski morskie,
paleo-mierzeje, Morze Bałtyckie

Streszczenie

Przeprowadzono pilotażowe prace nad koncentracją REE w piaskach bałtyckich za pomocą metodyki ICP-MS oraz mikrosondy elektronicznej (CAMECA SX-100). Analizy chemiczne składu jakościowego i ilościowego pierwiastków ziem rzadkich w próbkach piasków z koncentratów minerałów ciężkich z Ławicy Odrzanej oraz z Ławicy Słupskiej jak również z wkopu na plaży na Półwyspie Helskim (16,6 km plaży wybrzeża) osiągają zawartości REE, które mogą być interesujące pod względem surowcowym. Wyniki oznaczeń potwierdzają zależność koncentracji REE od procentowej zawartości minerałów ciężkich w osadach piasków morskich. Wskazują ponadto na monacyt jako główny wśród minerałów nośnik REE. W zbadanych próbkach koncentratów minerałów ciężkich oraz w próbce z Półwyspu Helskiego jest zdecydowana przewaga LREE. Najwyższe koncentracje osiąga głównie cer, a prawie dwukrotnie niższe lantan. Suma REE w wyżej wymienionych najciekawszych pod względem zawartości REE próbkach mieści się w zakresie od około 0,14% (wkop na plaży) do

około 0,9% (koncentrat z Ławicy Odrzanej). Wysokiej koncentracji REE towarzyszy wysoka zawartość Th (900–150 ppm). W próbkach koncentratu minerałów ciężkich pojawia się również neodym (0,1–0,17% Nd), którego obecność jest związana z pojawianiem się pirochloru oraz Nb-rutylu.

Konieczne jest systematyczne rozpoznanie zasobów minerałów ciężkich w piaskach bałtyckich. Dokładniejszymi badaniami powinny być objęte obszary perspektywiczne położone na północny wschód od pól złóżowych objętych dokumentacją zasobową „Ławica Odrzana”, wstępnie rozpoznane obszary na Ławicy Słupskiej oraz podwodny sklon (paleo-mierzeja) Półwyspu Helskiego.

RARE EARTH ELEMENTS PILOT STUDIES OF THE BALTIC SEA SANDS ENRICHED IN HEAVY MINERALS

Keywords

rare earth elements, heavy minerals, marine sands, paleo-shoals, Baltic Sea

Abstract

The carried out pilot work on the concentration of rare earth elements (REE) in the Baltic marine sands from the Odra and Słupsk Banks showed that in some places their accumulations are quite interesting in terms of the placer deposits and may be the subject of an interesting prospecting project. The results of ICP-MS and electron microprobe (CAMECA SX-100) investigation confirm the close relationship of REE concentration to heavy minerals content in the sediments of marine sands. It is indicated, in addition to monazite, as a primary mineral carrier of rare earth elements. The vast preponderance of light REE is noted in the samples of heavy mineral concentrates from the Odra and Słupsk Banks as well as in the beach sand sample from the Hel Peninsula. The highest concentrations are achieved mainly by cerium and almost two times less by lanthanum. The total REE in the most interesting considered samples range from c.a. 0.14% (trench on the beach) to 0.9% (heavy minerals concentrate from the Odra Bank). The high contents of REE are accompanied by a high concentration of Th (900–150 ppm). Neodymium (0.1–0.17% Nd), whose presence is associated with the presence of pyrochlore and Nb-rutile also appears in the heavy minerals concentrate samples. It is necessary to systematically identify heavy minerals resources in the Baltic sands. More detailed research should cover the prospective areas situated to the North-East from the documented placer fields of the Odra Bank, as well as tentatively identified areas of the Słupsk Bank and submarine paleo-slope of the Hel Peninsula.

