

ESMA KAHRAMAN^{1*}

STATISTICAL MODELS FOR PREDICTING THE MECHANICAL PROPERTIES OF LIMESTONE AGGREGATE BY SIMPLE TEST METHODS

The prediction of strength properties is a topic of interest in many engineering fields. The common tests used to evaluate rock strength include the uniaxial compressive strength test (*UCS*), Brazilian tensile strength (*BTS*) and flexural strength (*FS*). These tests can only be carried out in the laboratory and involve some difficulties such as preparation of the samples according to standards, amount of samples, and the long duration of test phases. This article aims to suggest equations for the prediction of mechanical properties of aggregates as a function of the P-wave velocity (*V_p*) and Schmidt hammer hardness (*SHH*) value of intact or in-situ rocks using regression analyses. Within the scope of the study, 90 samples were collected in the south of Türkiye. The mechanical properties, such as uniaxial compressive strength, Brazilian tensile strength and flexural strength of specimens, were determined in the laboratory and investigated in relation to P-wave velocity, and Schmidt hardness. Using regression techniques, various models were developed, and comparisons were made to find the optimum models using a coefficient of determination (*R*²) and *p* value (sig) performance indexes. Simple and multiple regression analysis found powerful correlations between mechanical properties and P-wave velocity and Schmidt hammer hardness. In addition, the prediction equations were compared with previous studies. The results obtained from this study indicate that the results of simple test methods, such as *V_p* or *SHH* values, of rock used for aggregate could be used to predict some mechanical properties. Thus, it will be possible to obtain information about the mechanical properties of aggregates in the study area in a faster and more practical way by using predictive models.


Keywords: Aggregate; P-Wave Velocity; Schmidt Hardness; Regression; Mechanical Properties

1. Introduction

Aggregates are the main raw material of engineering builds such as roads, tunnels, bridges, and seaports, so it is crucial to know the mechanical properties of aggregates for the strength

¹ ÇUKUROVA UNIVERSITY, TURKEY

* Corresponding author: ekahraman@cu.edu.tr

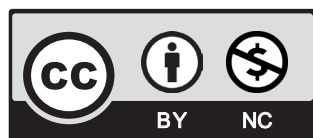

© 2023. The Author(s). This is an open-access article distributed under the terms of the Creative Commons Attribution-NonCommercial License (CC BY-NC 4.0, <https://creativecommons.org/licenses/by-nc/4.0/deed.en>) which permits the use, redistribution of the material in any medium or format, transforming and building upon the material, provided that the article is properly cited, the use is noncommercial, and no modifications or adaptations are made.

and usage time of the structure in which they are used. Classic test methods require a series of operations, such as a collection of rock samples by drilling in the study area, transporting the collected samples to the laboratory and preparing them following the standards. This situation causes losses of the workforce, energy and time during the determination of physico-mechanical properties. Contrary to standard methods, fast and reliable results obtained using practical and portable alternative simple methods will provide both in-situ and faster results. In addition, the most crucial advantage is that it does not cause deformations in the study area or rock mass. Studies have found that non-destructive and in situ testing methods, such as acoustic emission, seismic wave velocity, and certain hardness tests, can provide considerable benefits in mining, natural stone, and construction projects [1-14].

In previous studies, various indirect testing methods were employed by researchers for reliable estimation of physical and mechanical properties. However, currently, the Schmidt hammer hardness test (*SHH*) and P-wave velocity (*V_p*) methods are regular tests to predict the mechanical properties of limestone aggregate samples. *V_p* is a powerful variable, correlated with different physico-mechanical and index properties for rocks with various origins in many studies [4-19]. *SHH* was applied to estimate the empirical correlations between the mechanical properties obtained from classical tests for concrete and rocks [20-24].

Many studies proposed different models to estimate mechanical properties based on index tests such as ultrasonic wave velocity and various hardness tests because these mechanical properties are crucial for the evaluation of the use of rocks. But generally, researchers focused on statistical approaches for predicting *UCS*. Azimian et al. [5] showed there were strong relationships between *UCS* with point load index and *V_p* for marly rocks. Altindag [25] performed regression analysis to investigate the relationships between *V_p* and the physico-mechanical properties of sedimentary rocks. The relationships, such as *UCS-V_p*, *SHH-V_p*, point load index-*V_p*, *TS-V_p*, porosity-*V_p* and unit weight-*V_p*, were determined by using simple and multiple regression analyses. Yasar and Erdogan [26] improved empirical equations based on *V_p*. They correlated the *V_p*-density, *V_p*-*UCS* and *V_p*-Young's modulus of carbonate rocks. Yagiz [17] aimed to estimate *UCS* and some physico-mechanical properties by using the *V_p* value of rocks. Many researchers used *SHH* to estimate the relationships with mechanical properties obtained from standard tests for concrete and rocks [20-23]. Kahraman [27] correlated *UCS* with parameters such as point load index, *SHH* and *V_p* tests. *SHH* tests were used to estimate the empirical correlations between *SHH* values and *UCS* values obtained from standard tests for concrete and rocks [20-23].

This study focused on evaluating some in situ and simple methods, such as the Schmidt hardness test (*SHH*) and P-wave velocity (*V_p*) and utilised statistical techniques to estimate the uniaxial compressive strength (*UCS*), Brazilian tensile strength (*BTS*) and flexural strength (*FS*) of limestone aggregates. The studied limestone aggregate samples were collected from Mersin, Adana, and Osmaniye cities in the south of Türkiye. Simple and multiple regression analysis was applied to define the relationships between *UCS*, *BTS* and *FS* and *V_p*, as well as *SHH*. In addition, the obtained estimation equations were associated with previous studies. The analyses showed the existence of crucial and meaningful relationships between the investigated parameters. Thus, this study enables the determination of the mechanical properties of limestones from the study regions in a more practical way, economically and in a shorter time.

This paper covers previous studies on predictive models for mechanical properties. In section 3, sampling and experimental studies are introduced. In Section 4, the statistical analysis is discussed. In Section 5, comparisons with previous studies are made. Finally, the conclusions are drawn in Section 6.

2. Previous studies about predictive models for mechanical properties

Researchers proposed various models to estimate mechanical properties such as *UCS*, *BTS* and *FS* based on simple and in-situ tests because of their importance. In general terms, researchers focused on *BTS* and *UCS* parameters. However, studies about the estimation of *FS* are limited. Some of the most used correlations between mechanical properties and *SHH* or *V_p* are summarised in TABLE 1.

TABLE 1

Equations correlating some mechanical properties using *SHH* and *V_p*

Equation	R^2	Rock Type	References	Comment
$UCS = 35.54V_p - 55$ $UCS = 8.36SHH - 416$	0.80 0.87	19 different granite	Tugrul and Zarif [24]	<i>UCS</i> in MPa and <i>V_p</i> in km/s
$UCS = 4.24e0.059SHH$	0.81	Igneous, metamorphic and sedimentary rocks	Fener et al. [28]	<i>UCS</i> in MPa
$UCS = 64.2V_p - 11799$	0.90	Sandstone, coal, quartz micaschist, phyllite, basalt	Sharma and Singh [29]	<i>UCS</i> in MPa and <i>V_p</i> in m/s
$UCS = 0.026V_p - 20.47$	0.91	Marly rocks	Azimian and Ajalloeian [30]	<i>UCS</i> in MPa and <i>V_p</i> in m/s
$UCS = 4.53V_p^{2.23}$ $FS = 1.1V_p^{1.55}$	0.68 0.80	Tuffs	Teymen [31]	<i>UCS</i> and <i>FS</i> in MPa and <i>V_p</i> in km/s
$UCS = 0.25SHH^{1.77}$ $\ln UCS = 3.94 \ln V_p - 28.12$ $BTS = 0.15SHH^{1.33}$	0.88 0.92 0.83	Basalt and rhyolite	Kallu and Roghanchi [32]	<i>UCS</i> and <i>BTS</i> in MPa
$UCS = 0.1383SHH^{1.743}$	0.91	47 Different rock samples	Karaman and Kesimal [33]	<i>UCS</i> in MPa
$UCS = 2.304V_p^{2.43}$ $UCS = 0.0137SHH^{2.27}$ $BTS = 0.49V_p^{1.8723}$ $BTS = 0.10087SHH^{1.77}$	0.94 0.93 0.92 0.95	19 different Rock	Kılıç and Teymen, [34]	<i>UCS</i> and <i>BTS</i> in MPa and <i>V_p</i> in km/s
$BTS = 0.1722SHH^{1.4182}$ $BTS = 1.687V_p^{1.7271}$	0.80 0.68	Different types of limestone rocks	Mohammed et al. [35]	<i>BTS</i> in MPa and <i>V_p</i> in km/s
$UCS = 0.009V_p^{1.105}$ $UCS = 2.664SHH - 35.22$	0.92 0.92	Limestone rocks	Azimian [36]	<i>UCS</i> in MPa and <i>V_p</i> in m/s
$UCS = 0.033V_p - 34.63$ $BTS = 0.001V_p + 0.662$	0.87 0.88	Quartzite, Granite, Dolomite, Marble, Shale	Khandelwal [37]	<i>UCS</i> in MPa and <i>V_p</i> in m/s

TABLE 1. Continued

$BTS = 0.2182SHH - 0.5659$ $BTS = 0.0015V_p - 0.3164$	0.70 0.63	Different types of rocks	Parsajoo et al. [38]	BTS in MPa and V_p in m/s
$UCS = 0.03467V_p - 85.246$ $BTS = 0.003078V_p - 7.873$	0.85 0.85	basaltic rocks	Karakuş and Akatay [39]	UCS and BTS in MPa and V_p in m/s
$BTS = 2 \times 10^{-5} V_p^{1.5343}$	0.93	Granite	Francisco et al. [40]	BTS in MPa and V_p in m/s
$FS = 2.67e^{0.0023SHH}$	0.96	Concrete	Murthi et al. [41]	FS in MPa
$FS = 0.0041V_p - 9.6345$	0.72	Granite	Noor-E-Khuda et al. [42]	FS in MPa and V_p in m/s

Previous studies have shown that equations were estimated for *UCS*. This study focused on generating the prediction equations of the main mechanical tests such as *UCS*, *BTS* and *FS* by using some in situ and simple methods such as *SHH* and *V_p*.

3. Sampling And Experimental Studies

Sampling

In this paper, a total of 90 limestone samples were studied using materials taken from the south of Türkiye as aggregate. These limestone aggregate samples are from seven different localities that represent the limestone properties of the region (Fig. 1). Seven separate locations represent almost half of the Mediterranean region. At least 10 samples were obtained from each location, taking into account the structural changes. Samples were prepared from massive, discontinuous and unaltered parts by using wet abrasive cut-off machine and wet drilling machine.

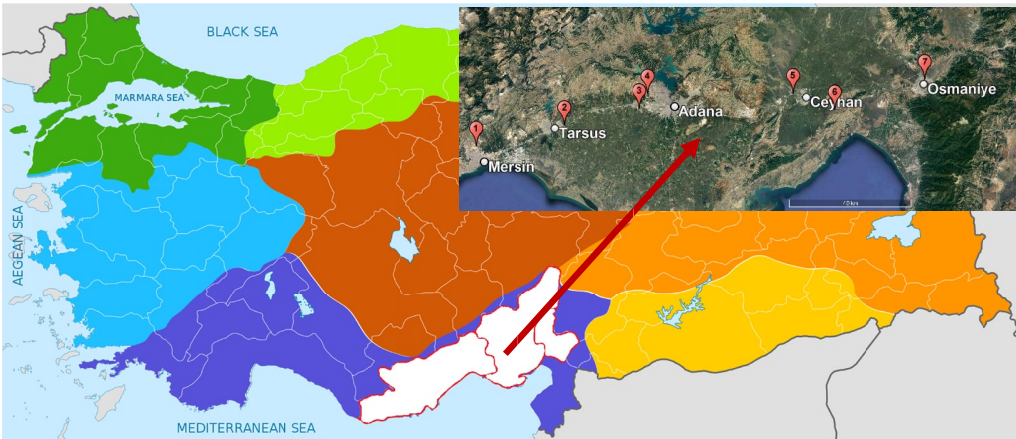


Fig. 1. Location of sample areas

Experiment studies

With the aim of the study, all limestone aggregate samples underwent physico-mechanical tests. These tests were uniaxial compressive strength (*UCS*), Brazilian tensile strength (*BTS*), flexural strength (*FS*), P-wave velocity (*Vp*) and Schmidt hammer hardness (*SHH*). The experiments were performed following the American Society for Testing Materials (ASTM) and the International Society for Rock Mechanics (ISRM) standards (TABLE 2).

TABLE 2

Applied tests and standards

Applied experiments	Standards
Uniaxial Compressive Strength (<i>UCS</i>)	ASTM D2938–95 [43]
Brazilian Tensile Strength (<i>BTS</i>)	ASTM D3967-16 [44]
Flexural Strength (<i>FS</i>)	ASTM C 880-89 [45]
Schmidt Hardness Test (<i>SHH</i>)	ISRM (1981b) [46]
P-Wave Velocity (<i>Vp</i>)	ISRM (1978) [47]

In experimental studies, a digital calliper (Accud 0-300 mm measuring range), drying oven (Memmert UN55 +5°C / 300°C measuring range), *BTS* test apparatus, *FS* test machine (ELE), pundit (Proceq PL-200), *UCS* machine (ELE-3000 kN capacity) and N-type *SHH* were used for physico-mechanical tests (Fig. 2).

A total of 90 tests were performed on samples obtained from 7 different regions. The average values obtained from these tests are given in TABLE 3. Also, the histograms of the *UCS*, *BTS*, *FS*, *Vp* and *SHH* values for the specimens are illustrated in Fig. 3.



Fig. 2. Physico-mechanical test machines and apparatus

TABLE 3

Ranges of experimental data

Variable	N	Minimum	Maximum	Mean	SD	Variance	Skewness	Kurtosis
USC (MPa)	90	17.57	68.25	41.35	15.23	231.86	0.08	−1.36
BTS (MPa)	90	1.19	11.63	7.56	2.81	7.91	−0.90	−0.37
FS (MPa)	90	0.82	12.53	6.27	3.75	14.08	0.38	−1.50
SHH	90	10.30	36.12	22.91	7.62	58.10	0.17	−1.31
Vp (km/s)	90	2.96	6.48	5.01	0.91	0.83	−0.47	−0.23

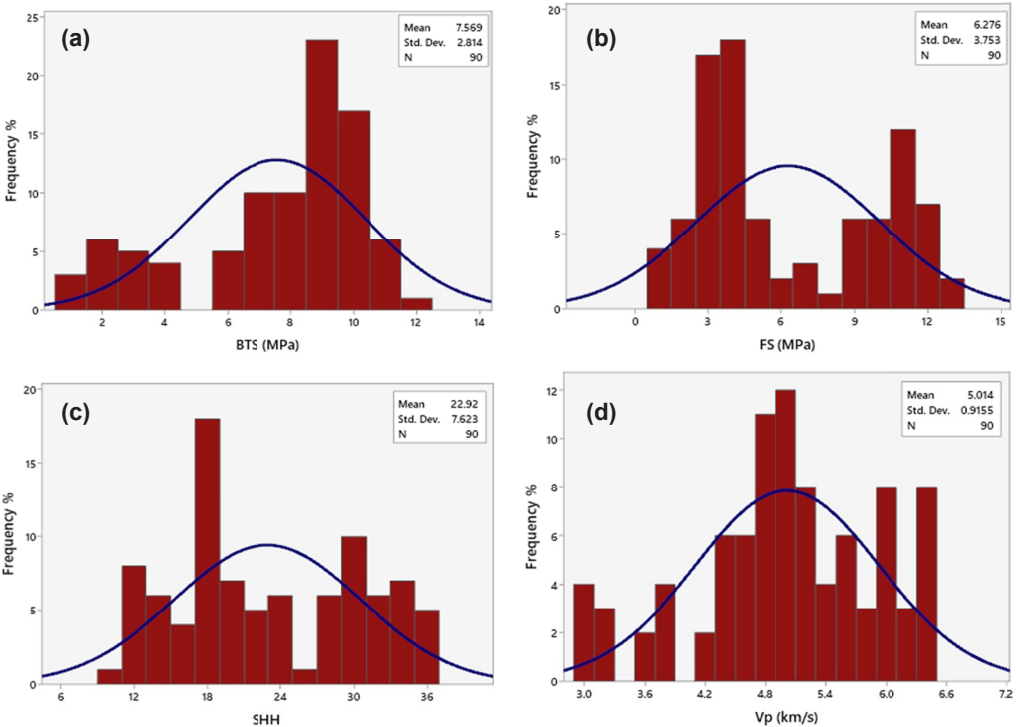


Fig. 3. Histograms of (a) *UCS*, (b) *BTS*, (c) *FS*, (d) *SHH* and (e) *Vp*

4. Statistical Analysis

This study utilised simple and multiple regression analyses, which are commonly used methods for estimating rock properties. The statistical analysis was performed using Minitab 19 statistical software, including ANOVA test results.

Simple regression analysis

SHH and *Vp* values were correlated with *UCS*, *BTS* and *FS* by weight using the method of least squares regression. Simple regression analyses were performed, and the equations of the

best-fit line, the determination coefficient (R^2) and the 95% confidence and prediction limits were determined for each regression. Simple regression analysis was performed to examine the relationship. Linear, logarithmic, exponential, and power curve fitting approximations were applied, and the highest correlation coefficient was determined for each regression. The ANOVA test results are detailed in TABLE 4 for the simple regression analyses. The p value was used to determine the significance level of the R^2 values of regression equations, and p values were below 0.005.

TABLE 4

ANOVA test results for simple regression analyses

Equation No	Dependent variable	Independent variables	B (Coeff.)	Standard Error	R^2	Itl value	F-value	p value
1	UCS	SHH	1.064	0.040	0.83	26.374	695.610	0.000
Power		Constant	1.465	0.454		8.021		0.000
2	UCS	V_p	1.827	0.086	0.84	21.232	450,788	0.000
Power		Constant	2.090	0.289		7.237		0.000
3	BTS	SHH	1.367	0.080	0.76	17.028	289.956	0.000
Power		Constant	0.102	0.025		4.033		0.000
4	BTS	V_p	2.609	0.095	0.89	27.338	747.387	0.000
Power		Constant	0.106	0.016		6.524		0.000
5	FS	SHH	1.857	0.052	0.93	35.897	1288.625	0.000
Power		Constant	0.017	0.003		6.257		0.000
6	Exponential	V_p	0.661	0.035	0.89	19.079	363.990	0.000
Exponential		Constant	0.186	0.033		5.668		0.000

A power correlation was found between UCS and SHH for all data (Fig. 4(a)). The correlation coefficient of the relationship was 0.83. Eq. (1) for the curve is:

$$UCS = 1.465 \times SHH^{1.064} \quad (R^2 = 0.83) \quad (1)$$

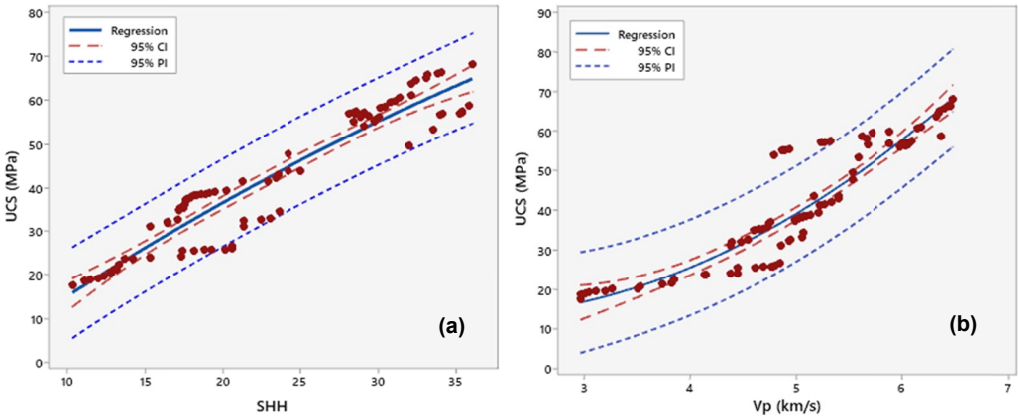


Fig. 4. Relationship between (a) SHH - UCS and (b) V_p - UCS of limestone aggregates

An exponential relationship was found between UCS and V_p for all data (Fig. 4(b)). The correlation coefficient of the relationship was 0.85. Eq. (2) for the curve is:

$$UCS = 2.090 \times V_p^{1.827} \quad (R^2 = 0.85) \quad (2)$$

As visible from Fig. 5(a) and Fig. 5(b), BTS demonstrated a power relationship with SHH and V_p , respectively. The correlation coefficient of the relationship between BTS and SHH was 0.76, and the correlation coefficient of the relationship between BTS and V_p was 0.89. Eq. (3) and Eq. (4) for the curve are

$$BTS = 0.102 \times SHH^{1.367} \quad (R^2 = 0.76) \quad (3)$$

$$BTS = 0.106 \times V_p^{2.609} \quad (R^2 = 0.89) \quad (4)$$

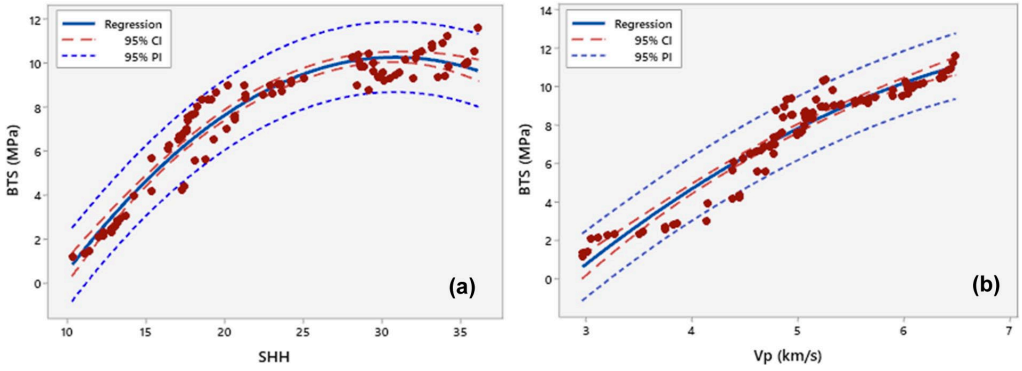


Fig. 5. The relationships between (a) SHH - BTS and (b) V_p - BTS of limestone aggregates

A power relationship was found between FS and SHH for the entire dataset (Fig. 6(a)). The correlation coefficient of the relationship was 0.93. Eq. (5) for the curve is:

$$FS = 0.017 \times SHH^{1.857} \quad (R^2 = 0.93) \quad (5)$$

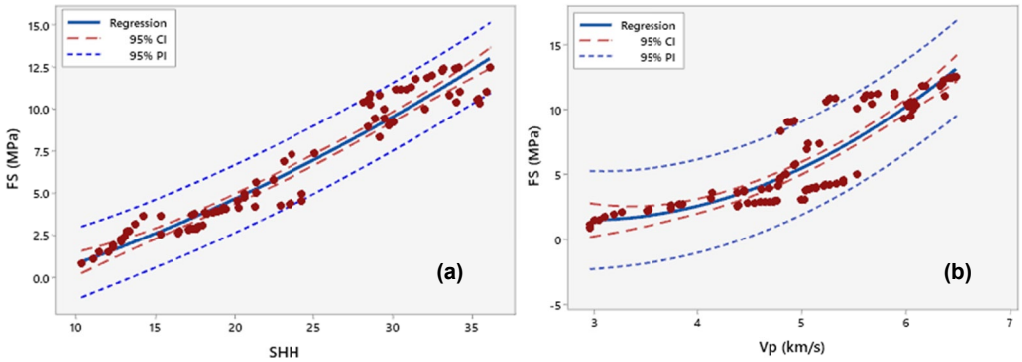


Fig. 6. The relationships between (a) SHH - FS and (b) V_p - FS of limestone aggregates

An exponential relationship was found between FS and SHH for the dataset (Fig. 6(b)). The correlation coefficient of the relationship was 0.89. Eq. (6) for the curve is:

$$FS = 0.186 \times e^{0.661V_p} \quad (R^2 = 0.89) \quad (6)$$

Multiple Regression Analyses

In the next stage of the regression analyses, a series of multiple regression analyses were performed using SHH and V_p . The ANOVA test results for the multiple regression models to predict the UCS , BTS and FS are summarised in TABLE 5.

TABLE 5

ANOVA test results for multiple regression analyses

Equation No	Independent variables	B (Coeff.)	Standard Error	R^2	ItI value	F-value	p value
7 <i>UCS</i>	Constant SHH V_p	-13.99	3.50	0.91	3.99	436.49	0.000
		1.374	0.149		9.24		0.000
		4.76	1.24		3.84		0.000
8 <i>BTS</i>	Constant SHH V_p	-6.117	0.677	0.90	19.079	363.990	0.000
		0.061	0.028		5.668		0.037
		2.451	0.239				0.000
9 <i>FS</i>	Constant SHH V_p	-3.466	0.769	0.92	4.51	561.390	0.000
		0.521	0.032		15.97		0.000
		-0.440	0.272		1.62		0.109

The equations derived to estimate UCS , BTS and FS of limestone aggregates can be listed as follows:

$$UCS = -13.99 + 1.374SHH + 4.76V_p \quad (7)$$

$$BTS = -6.117 + 0.061SHH + 2.451V_p \quad (8)$$

$$FS = -3.466 + 0.5214SHH - 0.44V_p \quad (9)$$

The relationships between the measured and predicted values are illustrated in Figs. 7-9. As can be seen, the prediction models appear to be more reliable than those obtained by simple regression analysis.

5. Comparison with previous researches

A comparison with the previous studies was done to verify the limitations of the various prediction models. Here, P-wave velocity and Schmidt hammer hardness values were placed in the prediction equations for UCS , BTS and FS and plotted against observed UCS , BTS and FS . There were significant changes between the predicted data and our observed data in each case because of sample differences.

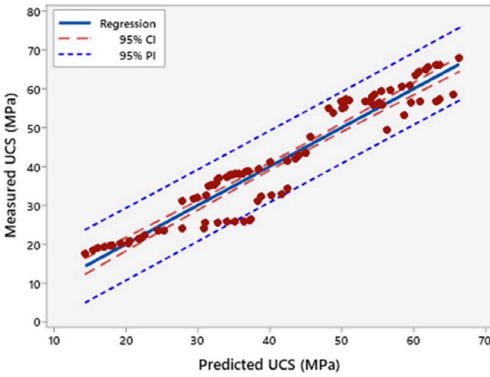


Fig. 7. The relationship between the measured and predicted *UCS* from multiple regression

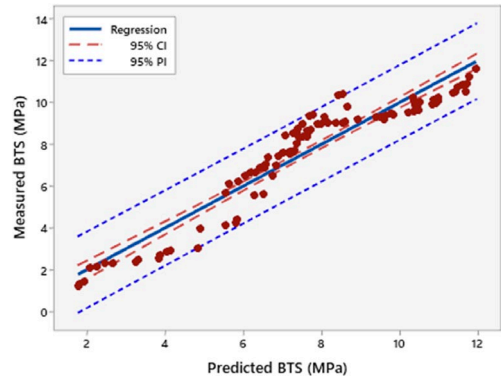


Fig. 8. The relationship between the measured and predicted *BTS* from multiple regression

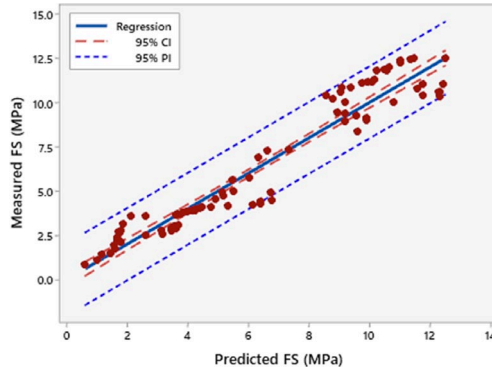


Fig. 9. The relationship between the measured and predicted *FS* from multiple regression

Fig. 10(a) shows *UCS* predicted using *SHH* by Fener et al. [28], Kallu and Roghanchi [32], Karaman and Kesimal [33] and Kilic and Teymen [34] with the observed dataset. The prediction equation suggested for *UCS* using *SHH* in this study differs from those suggested in other studies. However, a close relationship was observed to the prediction equation proposed by Karaman and Kesimal [33].

In Fig. 10(b), there are meaningful differences for *UCS* predicted using *V_p* by Yasar and Erdogan [26], Sharma and Singh [29], Kilic and Teymen [34] and Khandelwal [37]. The closest equation to the data obtained in this study was the one proposed by Kilic and Teymen [34].

As illustrated in Fig. 11(a), there were meaningful differences between *BTS* predicted using *SHH* by Kilic and Teymen [34], Kallu and Roghanchi [32], and Parsajoo et al. [38] with the observed dataset. Among the past studies, the closest to the results of the study was the study by Kallu and Roghanchi [32].

Fig. 11(b) shows *BTS* predicted using *V_p* by Kilic and Teymen [34], Khandelwal [37], Karakus and Akatay [39], and Francisco et al. [40] with the observed dataset. Overall, there are similar relationships observed except for the study conducted by Khandelwal [37].

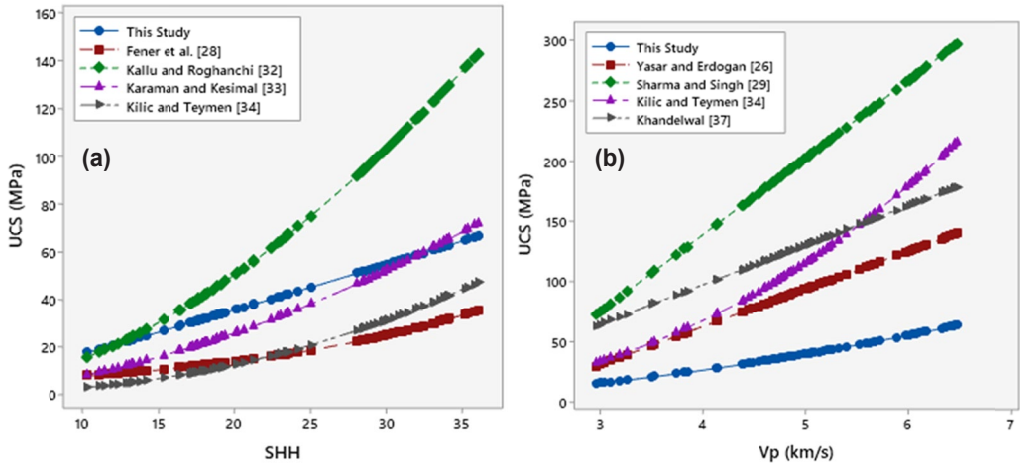


Fig. 10. Comparison of the derived equations with previous equations used to predict UCS using SHH (a) and (b) V_p

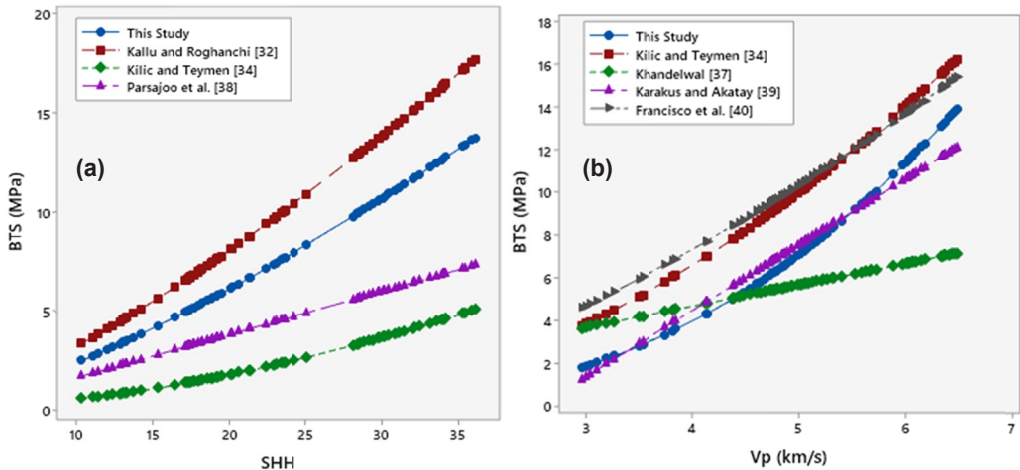


Fig. 11. Comparison of the derived equations with previous equations used to predict BTS using SHH (a) and (b) V_p

When previous studies are reviewed, few studies were identified using SHH and V_p for the estimation of FS .

Fig. 12(a) shows FS predicted using SHH by Teymen [31] and Noor-E-Khuda et al. [41], and Fig. 12(b) shows FS predicted using V_p by Murthi et al. [42].

The studies investigated are related to rocks and concrete with different origins. This situation creates differences between the obtained equations. In addition, since the intervals of the data obtained as a result of the experiments are variable, the accuracy of the estimation will decrease for higher and lower values.

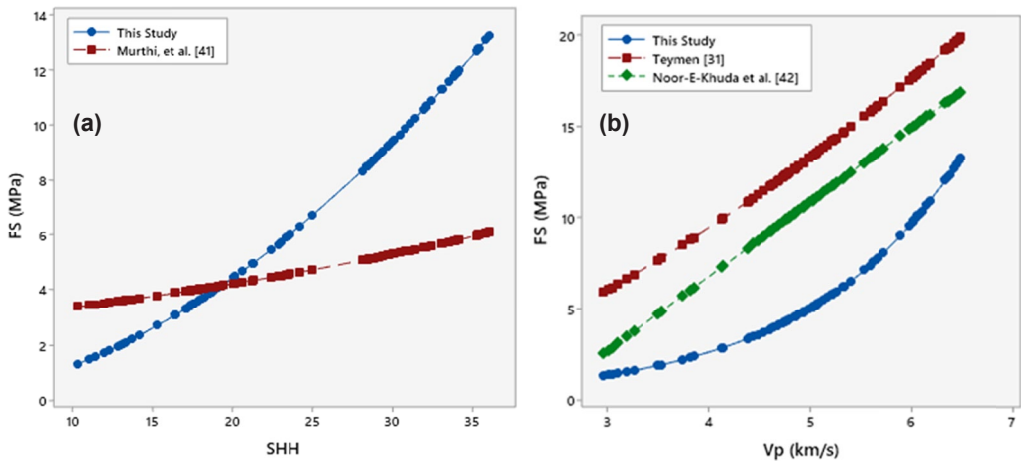


Fig. 12. Comparison of the derived equations with previous equations used to predict FS with SHH (a) and (b) V_p

This study took into account the specific characteristics of rocks in the region. Estimated equations created for the study region can be used. However, the evaluation of a larger study area will require a more comprehensive evaluation in future studies. Because the rock physico-mechanic properties of different places and environments are different.

6. Conclusion

In this study, simple test methods (V_p and SHH) and mechanical properties (UCS - BTS and FS) of the rocks used for limestone aggregate were determined for 90 limestone aggregate samples. Secondly, regression analysis was used to correlate the obtained parameters, and regression equations were established for the studied properties. In addition, multiple regression analysis showed high prediction performance for the prediction of UCS , BTS and FS . Furthermore, the study's estimation equations were compared to those of previous studies.

In conclusion, V_p and SHH methods have significant statistical correlations with the mechanical properties of limestone aggregates due to high correlation coefficients. The results of this study indicate that UCS , BTS and FS values can be predicted by determining SHH and V_p , which are simple, practical, less time-consuming and economical methods. The suggestion is that Schmidt hardness and P-wave velocity may be used most confidently for prediction of mechanical properties. It is suggested that the experimental investigation should be repeated with a number of different rock types in order to universalise these statistical relations. Further study is required to see how varying the rock type affects the correlations.

Declaration of Competing Interest

The author declares that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgments

The author thanks the Research Fund Project (FBA-2022-15024) of Çukurova University for their financial support in this study. The corresponding author also wishes to thank the reviewers for their helpful suggestions, which led to a great improvement of this paper.

References

- [1] I. Korobiichuk, V. Korobiichuk, P. Hajek, P. Kokes, A. Juś, R. Szewczyk, Investigation of leznikovskiy granite by ultrasonic methods. *Arch. Min. Sci.* **63** (1), 75-82 (2018). DOI: <https://doi.org/10.24425/118886>
- [2] L. Dong, X. Tong, J. Ma, Quantitative investigation of tomographic effects in abnormal regions of complex structures. *Engineering* **7** (7), 1011-1022 (2021). DOI: <https://doi.org/10.1016/j.eng.2020.06.021>
- [3] Y.B. Zhang, X.L. Yao, P. Liang, K.X. Wang, L. Sun, B.Z. Tian, S.Y. Wang, Fracture evolution and localization effect of damage in rock based on wave velocity imaging technology. *J. Cent. South Univ.* **28** (9), 2752-2769 (2021). DOI: <https://doi.org/10.1007/s11771-021-4806-7>
- [4] A. Kos, J. Kortnik, Ultrasonic quality inspection of dimension stone blocks compactness. *Arch. Min. Sci.* **64** (2), 415-428 (2019). DOI: <https://doi.org/10.24425/ams.2019.128692>
- [5] A. Azimian, R. Ajalloeian, L. Fatehi, An Empirical Correlation of Uniaxial Compressive Strength with P-Wave Velocity and Point Load Strength Index on Marly Rocks Using Statistical Method. *Geotech. Geol. Eng.* **32** (1), 205-214 (2014). DOI: <https://doi.org/10.1007/s10706-013-9703-x>
- [6] K. Diamantis, E. Gartzos, G. Migiros, Study on Uniaxial Compressive Strength, Point Load Strength Index, Dynamic and Physical Properties of Serpentinities from Central Greece: Test Results and Empirical Relations. *Eng. Geol.* **108**, 199-207 (2009). DOI: <https://doi.org/10.1016/j.enggeo.2009.07.002>
- [7] M.T. Fener, The Effect of Rock Sample Dimension on the P-Wave Velocity. *Non. Destruct. Eval.* **30**, 99-105 (2011). DOI: <https://doi.org/10.1007/s10921-011-0095-7>
- [8] P. Gaviglio, Longitudinal Wave Propagation in a Limestone: The Relationship between Velocity and Density. *Rock Mech. Rock Eng.* **22**, 299-306 (1989). DOI: <https://doi.org/10.1007/BF01262285>
- [9] S. Kahraman, T. Yeken, Determination of Physical Properties of Carbonate Rocks from P-Wave Velocity. *Bull. Eng. Geol. Environ.* **67**, 277-281 (2008). DOI: <https://doi.org/10.1007/s10064-008-0139-0>
- [10] M. Khandelwal, P.G. Ranjith, Correlating Index Properties of Rocks with P-Wave Measurements. *J. Appl. Geophys.* **71**, 1-5 (2010). DOI: <https://doi.org/10.1016/j.jappgeo.2010.01.007>
- [11] M. Khandelwal, T.N. Singh, Correlating Static Properties of Coal Measures Rocks with P-Wave Velocity. *Int. J. Coal Geol.* **79**, 55-60 (2009). DOI: <https://doi.org/10.1016/j.coal.2009.01.004>
- [12] R.D. Lama, V.S. Vutukuri, S.S. Saluja, Handbook on Mechanical Properties of Rocks, 2nd edn. Trans. Tech. Publications, Germany (1978).
- [13] J. Martínez-Martínez, D. Benavente, M.A. García-del-Cura, Comparison of the Static and Dynamic Elastic Modulus in Carbonate Rocks. *Bull. Eng. Geol. Environ.* **71**, 263-268 (2012). DOI: <https://doi.org/10.1007/s10064-011-0399-y>
- [14] B. Minaeian, K. Ahangari, Estimation of Uniaxial Compressive Strength Based on P-Wave and Schmidt Hammer Rebound Using Statistical Method. *Arab. J. Geosci.* **6**, 1925-1931 (2011). DOI: <https://doi.org/10.1007/s12517-011-0460-y>
- [15] Z.A. Moradian, M. Behnia, Predicting the Uniaxial Compressive Strength and Static Young's Modulus of Intact Sedimentary Rocks Using the Ultrasonic Test. *Int. J. Geomech.* **9**, 1-14 (2009). DOI: [https://doi.org/10.1061/\(ASCE\)1532-3641\(2009\)9:1\(14\)](https://doi.org/10.1061/(ASCE)1532-3641(2009)9:1(14))
- [16] K. Sarkar, V. Vishal, T.N. Singh, An Empirical Correlation of Index Geomechanical Parameters with the Compressional Wave Velocity. *Geotech. Geol. Eng.* **30** (2), 469-479 (2012). DOI: <https://doi.org/10.1007/s10706-011-9481-2>
- [17] S. Yagiz, P-wave Velocity Test for Assessment of Geotechnical Properties of Some Rock Materials. *Bull. Mater. Sci.* **34** (4), 947-953 (2011). DOI: <https://doi.org/10.1007/s12034-011-0220-3>

- [18] I. Yilmaz, A. G. Yuksek, An Example of Artificial Neural Network Application for Indirect Estimation of Rock Parameters. *Int. J. Rock. Mech. Min. Sci.* **5** (41), 781-795 (2008). DOI: <https://doi.org/10.1007/s00603-007-0138-7>
- [19] A.M. Kilic, E. Kahraman, O. Kilic, The Use Of Ultrasonic Meseasurements Determining the Quality of The Dimension Stone Blocks. *Int. J. Nat. Eng. Sci.* **11**, 28-33 (2017).
- [20] J.S. Cargill, A. Shakoor, Evaluation of Empirical Methods for Measuring the Uniaxial Compressive Strength. *Int. J. Rock Mech. Min. Sci.* **27**, 495-503 (1990).
- [21] V.A. Hucka, Rapid Method for Determining the Strength of Rocks in Situ. *Int. J. Rock. Mech. Min. Sci.* **2**, 127-134 (1965).
- [22] D.C. Entwisle, P.R.N. Hobbs, L.D. Jones, D. Gunn, M.G. Raines, The Relationships between Effective Porosity, Uniaxial Compressive Strength and Sonic Velocity of Intact Borrowdale Volcanic Group Core Samples from Sellafield. *Geotech. Geol. Eng.* **23**, 793-809 (2005). DOI: <https://doi.org/10.1007/s10706-004-2143-x>
- [23] R. Abdelaali, B. Abderrahim, B. Mohamed, G. Yves, S. Abderrahim, H. Mimoun, S. Jamal, Prediction of Porosity and Density of Calcarene Rocks from P-Wave Velocity Measurements. *Int. J. Geol.* **4**, 1292-1299 (2013). DOI: <https://doi.org/10.4236/ijg.2013.49124>
- [24] A. Tugrul, I.H. Zarif, Correlation of Mineralogical and Textural Characteristics with Engineering Properties of Selected Granitic Rocks from Turkey. *Eng. Geol.* **51**, 303-317 (1999). DOI: [https://doi.org/10.1016/S0013-7952\(98\)00071-4](https://doi.org/10.1016/S0013-7952(98)00071-4)
- [25] R. Altindag, Correlation between P-Wave Velocity and Some Mechanical Properties for Sedimentary Rocks. *J. South. Afr. Inst. Min. Metall.* **112** (3), 229-237 (2012).
- [26] E. Yasar, Y. Erdogan, Correlating Sound Velocity with the Density, Compressive Strength and Young's Modulus of Carbonate Rocks. *Int. J. Rock Mech. Min.* **41** (5), 871-875, (2004). DOI: [https://doi.org/10.1016/S0013-7952\(98\)00071-4](https://doi.org/10.1016/S0013-7952(98)00071-4)
- [27] S. Kahraman, Evaluation of Simple Methods for Assessing the Uniaxial Compressive Strength of Rock. *Int. J. Rock Mech. Min. Sci.* **38**, 981-994 (2011). DOI: [https://doi.org/10.1016/S1365-1609\(01\)00039-9](https://doi.org/10.1016/S1365-1609(01)00039-9)
- [28] M. Fener, S. Kahraman, A. Bilgil, O. Gunaydin, A Comparative Evaluation of Indirect Methods to Estimate the Compressive Strength of Rocks. *Rock. Mech. Eng.* **38** (4), 329-343 (2005). DOI: <https://doi.org/10.1007/s00603-005-0061-8>
- [29] P.K. Sharma, T.N. Singh, A Correlation between P-Wave Velocity, Impact Strength Index, Slake Durability Index and Uniaxial Compressive Strength. *Bull. Eng. Geol. Environ.* **67**, 17-22 (2008). DOI: <https://doi.org/10.1007/s10064-007-0109-y>
- [30] A. Azimian, R. Ajalloeian, Empirical Correlation of Physical and Mechanical Properties of Marly Rocks with P Wave Velocity. *Arab. J. Geosci.* **8** (4), 2069-2079 (2015). DOI: <https://doi.org/10.1007/s12517-013-1235-4>
- [31] A. Teymen, Prediction of Basic Mechanical Properties of Tuffs Using Physical and Index Tests. *J. Min. Sci.* **54** (5), 721-733 (2018). DOI: <https://doi.org/10.1134/S1062739118054820>
- [32] R. Kallu, P. Roghanchi, Correlations between Direct and Indirect Strength Test Methods. *Int. J. Min. Sci. Technol.* **25** (3), 355-360 (2015). DOI: <https://doi.org/10.1016/j.ijmst.2015.03.005>
- [33] K. Karaman, A. Kesimal, A Comparative Study of Schmidt Hammer Test Methods for Estimating the Uniaxial Compressive Strength of Rocks. *Bull. Eng. Geol. Environ.* **74**, 507-520 (2014). DOI: <https://doi.org/10.1007/s10064-014-0617-5>
- [34] A. Kilic, A. Teymen, Determination of Mechanical Properties of Rocks Using Simple Methods. *Bull. Eng. Geol. Environ.* **67** (2), 237-244 (2008). DOI: <https://doi.org/10.1007/s10064-008-0128-3>
- [35] D.A. Mohammed, Y.M. Alshkane, Y.A. Hamaamin, A.O. Mahmood, Tensile Strength of Different Types of Limestone Rocks in North of Iraq. *Innov. Infrastruct. Solut.* **7** (1), 1-16 (2022). DOI: <https://doi.org/10.1007/s41062-021-00620-y>
- [36] A. Azimian, Application of Statistical Methods for Predicting Uniaxial Compressive Strength of Limestone Rocks Using Nondestructive Tests. *Acta Geotech.* **12** (2), 321-333 (2017). DOI: <https://doi.org/10.1007/s11440-016-0467-3>
- [37] M. Khandelwal, Correlating P-Wave Velocity with the Physico-Mechanical Properties of Different Rocks. *Pure Appl. Geophys.* **170** (4), 507-514 (2013). DOI: <https://doi.org/10.1007/s00024-012-0556-7>
- [38] M. Parsajoo, D.J. Armaghani, A.S. Mohammed, M. Khari, S. Jahandari, Tensile Strength Prediction of Rock Material Using Non-Destructive Tests: A Comparative Intelligent Study. *Transp. Geotech.* **31**, 100652 (2021). DOI: <https://doi.org/10.1016/j.trgeo.2021.100652>

- [39] A. Karakuş, M. Akatay, Determination of Basic Physical and Mechanical Properties of Basaltic Rocks from P-Wave Velocity, *Nondestruct. Test Eval.* **28**, 342-353 (2013). DOI: <https://doi.org/10.1080/10589759.2013.823606>
- [40] M. Francisco, V. Graça, M. Tiago, The Performance of Ultrasonic Pulse Velocity on the Prediction of Tensile Granite Behaviour: A Study Based on Artificial Neural Networks, In: 9th International masonry conference in Guimarães, Portugal, (2014).
- [41] P. Murthi, K. Poongodi, R. Gobinath, Correlation between Rebound Hammer Number and Mechanical Properties of Steel Fibre Reinforced Pavement Quality Concrete. *Mater. Today: Proc.* **39**, 142-147 (2021). DOI: <https://doi.org/10.1016/j.matpr.2020.06.402>
- [42] S. Noor-E-Khuda, F. Albermani, M. Veidt, Flexural Strength of Weathered Granites: Influence of Freeze and Thaw Cycles. *Constr. Build. Mater.* **156**, 891-901 (2017). DOI: <https://doi.org/10.1016/j.conbuildmat.2017.09.049>
- [43] ASTM, D 2938-95: Standard Test Methods for Unconfined Compressive Strength of Intact Rock Core Specimens. ASTM, Race Street, Philadelphia PA 19103-1187, USA (2004).
- [44] ASTM D3967-16: Standard Test Method for Splitting Tensile Strength of Intact Rock Core Specimens, ASTM, Race Street, Philadelphia, USA, (2016).
- [45] ASTM C 880-89: Standard test method for flexural strength of dimensional stone. Annual book of ASTM Standards, ASTM 1916, Race Street, Philadelphia PA 19103-1187 USA, 04.08, (1993).
- [46] ISRM (International Society for Rock Mechanics) 1981b: Suggested Methods for Determining Hardness and Abrasiveness of Rocks, Part 3. Commission on Standardisation of Laboratory and Field Tests, 101-102, (1981).
- [47] ISRM (International Society for Rock Mechanics) 1978: Suggested methods for determining sound velocity. *Int. J. Rock Mech. Min. Sci. Geomech. Abstr.* **15**, 53-58, (1978).