



Industrial Recycling of Scrap Copper Cables and Wires: Combining Cold and Hot Treatments for Maximum Recovery and Minimal Emissions

O. Choukri *, E. Mohsine, S. Taibi

Department of Mechanical Engineering, Mohammadia School of Engineers, Morocco

* Corresponding author: E-mail address: o.choukri@emi.ac.ma

Received 21.10.2024; accepted in revised form 05.12.2024; available online 31.12.2024

Abstract

With the increasing amount of electrical cable and wire scrap, copper recycling has become a priority to conserve natural resources and reduce environmental impact. This study presents an innovative process for recycling copper wire and cable of various types, including greased ones. The process combines cold and hot treatments to maximise metal recovery while minimising polluting emissions. Initially, the cables are stripped and the PVC sheaths and other components are separated. Subsequently, these cables are subjected to pyrolysis in a hermetical furnace operating under an inert atmosphere, ensuring the absence of toxic emissions.

The pyrolysis, carried out at temperatures between 500 °C and 600 °C, decomposed the insulating materials while minimising copper oxidation. A 100 kg sample of wire and cable pyrolysed at 540 °C was melted in an Indian foundry using the Upcast process to produce 8 mm oxygen-free copper rods. The electrical conductivity measurement of these rods showed a value of 98.2% IACS, making them suitable for many applications, especially electrical ones. The copper recovery rate reached a maximum value of 99.5%, demonstrating the effectiveness of the process. This sustainable process, suitable for small and medium foundries, offers an efficient and environmentally friendly solution for copper cables recycling.

Keyword: Copper recycling, Greased cables, Cold treatment, Pyrolysis process, Greased cables, Upcast process

1. Introduction

The circular management of natural resources is essential to ensure their long-term availability. The application of recovery and recycling technologies will play a central role in promoting sustainable development worldwide [1-2]. The rapid development of the energy and information technology (IT) sectors has contributed significantly to the increased production and use of cables, which consume a significant proportion of the world's copper [3-7]. This growth has led to an increase in cable scrap, for

example in Germany over 150,000 tonnes are generated annually [8]. This highlights the importance of recycling these materials to conserve resources and protect the environment [9-10].

In addition to enamelled wires, copper cables recycled by most non-ferrous metal foundries are classified into five categories according to their manufacturing process, functions and usage characteristics: magnetic wires, bare wires, electrical wires and cables, power cables and communication cables [11]. These single-pole or multi-pole cables, with a lifespan ranging from 10 to 30 years, generally consist of a conductive, insulation, auxiliary



element, mechanical protection, shielding, armouring and PVC outer sheath [12-13]. The conductor core is made from industrially pure copper or oxygen-free copper with a purity of over 99.90%, with excellent electrical and thermal conductivity and excellent chemical stability, and accounting for 58.3% to 75% of a cable's total weight [13-14].

In addition to incineration, a traditional method of waste recycling involves open combustion, where the copper fraction is recovered from the remaining ashes [14] and the burned plastic residue releases energy [15] as well as toxic gases into the environment [16-17]. Semi-mechanized or mechanized processing techniques are used to separate copper from the insulating layers of large diameter cables, which have stable composition and uniform specifications [18-19]. Specific techniques are used to recycle mixed type cables with different compositions of insulating layers and intermediate or small diameters. These multi-step techniques generally involve mechanical methods (such as the use of ultrasonic [20] or hot water processes [21] combined with a mixer to dismantle the cables, followed by electrostatic separation [22-23], particle size classification [24], flotation [25] or dense separation [13] to isolate plastic and copper components), chemical methods (such as dissolution and cementation [26], chemical or biological leaching [27] and chloride volatilization [28]) and/or processes of energy recovery (such as steam gasification [14] and pyrolysis [29-31]).

Pyrolysis involves the chemical decomposition or transformation of a material into one or more substances at high temperatures in an inert atmosphere. This process is widely used to recycle enamelled wires and copper cables, as it enables the recovery not only of the metals but also of their protective elements (sheaths and insulators) [1-32]. The sheaths, mainly made of polyvinyl chloride (PVC), must be processed carefully during disposal to minimise the negative effects of their components, such as lead (Pb)-based stabilisers, phthalate plasticisers [33], mercury (Hg), cadmium (Cd), hexavalent chromium (Cr (VI)), polybrominated biphenyls and polybrominated diphenyl ethers [34]. In addition, the pyrolysis of PVC releases toxic organohalogen compounds and generates large quantities of

hydrochloric acid (HCl), which can cause material damage and pose serious environmental problems [35].

The plastic-to-metal ratios of electrical cables are typically ~ 45% and ~ 55% by weight, depending on their use and specifications [1-36]. Previous studies [1,8,14] have reported recycling recovery rates ranging from 95 % to 99.85 % for certain types of cables, including cable bundles with diameters between 0.5 to 2.5 cm and tinned copper. These studies involve expensive specialised equipment and techniques that make industrialisation challenging [37-38]. To improve the copper recovery rate and the level of purity obtained, this study will test a pyrolysis recycling process accessible to small foundries. This economic and Low environmental impact process will treat all types of copper wire and cable in large quantities, including those containing grease and oil, which are difficult to recover.

2. Methodology

A 100 kg batch of copper wire and sheathed cables was randomly selected from the copper scrap commonly received by Bonomar Company, specialising in non-ferrous metal recycling. The batch, consisting of enamelled wires and various cables for the transportation of electrical voltage or communication, was manually sorted by qualified operators based on multiple criteria such as dimension, shielding (steel or aluminum), grease (Fig.1), and other physical characteristics. These cables were then cut into one to two meter lengths using hydraulic and mechanical shears, and classified into different categories:

- A: Greased wires of various diameters.
- B: Greased cables with shielding (steel or aluminium).
- C: Carrier cables.
- D: Groove.
- E: Sheathed cables (without shielding or grease).
- F: Fibre-optic cables.

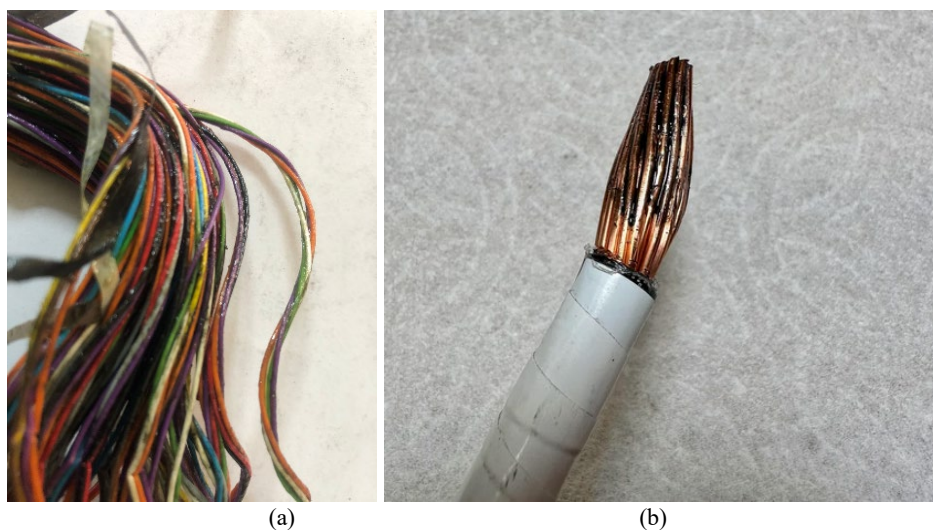


Fig.1. Greased cables a) greased wires, b) greased wires with shielding

2.1. Cold treatment

Class A, B and D cables are then stripped using a stripping machine, which separates the PVC sheath from the internal metal wires (Fig.2). The stripped materials are then sorted manually by operators on a conveyor belt. They separate the PVC, the shielding,

the ceramic paper and the copper wires. The grease present on some cables partially sticks to the wires and the insulation. PVC, class F cables and metal components such as steel or aluminium shielding are separated and sent to specialised units. Enamelled wires and those covered with plastic and grease are placed on a grid and pyrolysed in a furnace. Class C cables are not treated with this treatment.

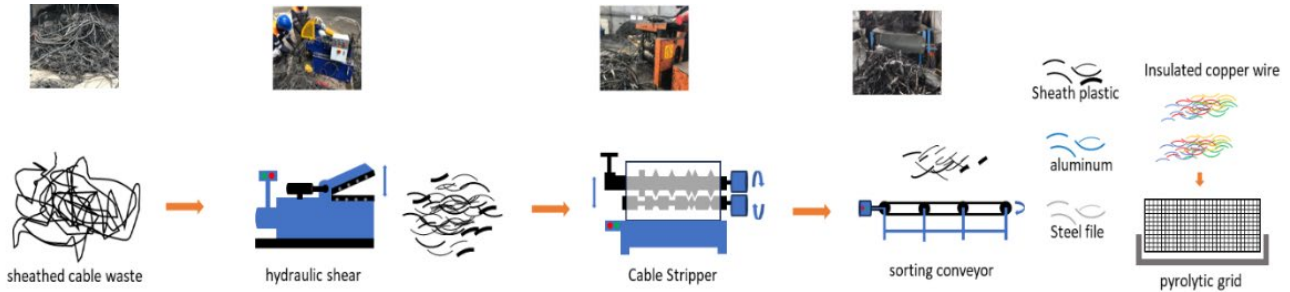


Fig.2. The Stages of Cold Treatment

2.2 Hot treatment (Pyrolysis)

The pyrolysis process (Fig.3), lasting between 90 and 140 minutes, begins with the insertion of the grid into the furnace. This hermetic furnace, with a maximum capacity of one ton and a total power consumption of 45 kwh, designed to operate on solar energy and prevent gas emission.

Before starting the heating process, the furnace is purged with nitrogen from a dedicated generator to establish an inert atmosphere. This purging lasts about 30 minutes, calculated based on the volume of the furnace, with an injection pressure of 10 bars. Once the atmosphere is saturated with nitrogen, the electric heating begins. The furnace temperature is then gradually increased until it reaches the pyrolysis range, between 500 and 600 °C. This furnace is designed to increase the temperature by 16°C every two minutes.

During the pyrolysis process, a continuous flow of nitrogen is maintained at a rate of 6 litres per minute to ensure an oxygen-free environment. Heating is stopped when the pyrolysis temperature is reached. The furnace cannot be opened until the temperature has dropped to around 180°C to prevent ignition of the gases and organic residues [39]. After complete cooling, the grid is removed from the furnace and the treated copper wire and cable are recovered. Organic residues (plastic, grease, and powder) fall into a bag at the bottom of the furnace, where they are collected as plates or pieces.

The extracted copper wire and cable is washed with water in a rotating drum to remove any traces of powder. After air-drying, the scrap is compacted into bundles using a hydraulic press. These bundles were sent to a foundry in India to produce 8mm oxygen-free rods using the upcast process.

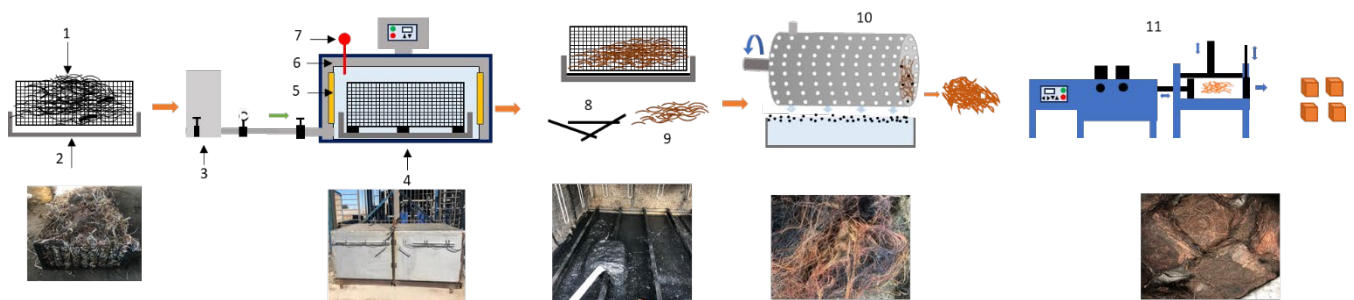


Fig. 3. Stages of Hot Treatment (Pyrolysis): 1- Insulated copper wire, 2- Pyrolytic grid, 3- Nitrogen, 4- Hermetic furnace, 5- Resistor, 6- Insulation, 7- Thermocouple, 8- Organic substance, 9- Copper, 10- Washing drum, 11- Press wire

2.3 Conductivity measurement

The conductivity of these rods was measured by a conductivity meter in a private laboratory. Before each test, this instrument is calibrated with reference samples of known conductivity. Ambient conditions, such as temperature, are measured because they have a direct influence on conductivity.

To test a sample of these rods, it was chemically cleaned by immersion in a dilute acid (sulphuric acid (H₂SO₄) or nitric acid (HNO₃)). After being rinsed with distilled water, the sample is cut to a specific length (often a few tens of centimeters from 100 to 500 mm) for homogeneous testing.

These segments are then connected to a specific electrical circuit via electrodes (from 1 to 100 mA) to measure their electrical resistance (R). Conductivity is then determined by the relationship:

$$\sigma = 1/\rho \text{ with } \rho = R \times (L/A)$$

- R : Resistance (ohms),
- A : Area of the rod (m²),
- L : Length of the rod (m).

3. Results Discussion

3.1 Residue Analysis

In general, the wire and cable pyrolysis process involves two distinct phenomena corresponding to temperature ranges of 300°C

to 400°C and 450°C to 550°C [37]. The first range is associated with the dechlorination of PVC sheaths and insulators, during which undesirable hydrogen chloride (HCl) is released due to the thermal decomposition of PVC. This process can be represented by the reaction: PVC → PVC_{dechlorinated} + HCl.

At the end of this step, we obtain a less toxic and more stable PVC_{dechlorinated} residue. In the second temperature range, the remaining organic components in the PVC_{dechlorinated} begin to decompose further in the absence of oxygen. This decomposition generates several products, including: hydrogen (H₂), methane (CH₄), carbon monoxide (CO), carbon dioxide (CO₂) and coal (solid residue). This decomposition maximises the conversion of carbon chains into combustible gases, producing mainly light hydrocarbons.

The cold treatment applied to the cables from the beginning significantly reduced the presence of chlorinated materials, particularly PVC, thus minimising the risks of toxic emissions and the generation of hydrochloric acid (HCl). The presence of this acid could lead to corrosion of the furnace and the release of harmful gases, notably organohalogen compounds, posing serious environmental problems [37,40,41]. This treatment has made the pyrolysis process not only more efficient, but also more economical for small foundries.

This is confirmed by the analysis of three samples of pyrolysis residues by X-Ray fluorescence (FX) (tab.1) and ICP (tab.2). The results of these analyses clearly show that most of the elements present in the residues are flame retardants (antimony trioxide (Sb)), thermal stabilisers (based on zinc (Zn), tin (Sn) and lead (Pb)), pigments (titanium oxide (Ti)) fillers (calcium-based calcined clay and calcium carbonate), additives (Al₂O₃, SiO₂ and K₂O), mineral fillers (MgO) and secondary phosphorus antioxidants (P₂O₅) [30,42,43].

Table 1.
Results (Wt. %) of Powder Residue Analysis by fluorescence X (Fx)

	Al ₂ O ₃	C	CaO	Cl	Cu	Fe ₂ O ₃	K ₂ O	MgO	P ₂ O ₅	Pb	S	SiO ₂	TiO ₂	Zn
Test ₁	3.67	48.97	1.59	0.93	1.05	1.82	0.06	0.36	0.2	2.6	0.34	17.19	1.17	0.8
Test ₂	4.1	41.45	1.32	0.81	0.71	1.77	0.01	0.33	0.2	3.34	0.41	11.68	0.98	0.71
Test ₃	3.77	47.13	1.63	0.95	0.89	1.81	0.07	0.33	0.13	2.1	0.22	15.77	1.08	0.76

Table 2.
Results (Wt. %) of Powder Residue Analysis by ICP

	AS	Li	Mo	Cd	Co	Ni	Sb	Sn	Sr	Y
Test ₁	<9	<3	<10	2	1	11	14	89	5	3
Test ₂	<9	<3	<10	2	1	9	13	77	5	3
Test ₃	<9	<3	<10	2	2	9	14	92	5	3

The low chlorine content of approximately 0.9 wt.%, combined with an ash content of approximately 45.85 wt.% and the presence of non-oxidized metals, gives pyrolysis residues considerable recycling potential. This favorable chemical composition opens the way to various industrial applications, allowing this residue to be used as a secondary raw material. For example, it is sometimes used in applications such as composite material and cement manufacturing [37-44]. The reuse of pyrolysis residues not only promotes the sustainable management of industrial waste, but also contributes to a circular economy by optimizing the use of available resources.

3.2 Pyrolysis product analysis

During the pyrolysis process, oxidation of the final product can occur even when working in an inert atmosphere. This oxidation can be caused by the presence of residual oxygen in the oven due to an imperfect seal or to low quantities of oxygen in the inert gas. This can also be attributed to heating, as a small amount of oxygen at temperatures above 600°C can cause significant oxidation of copper.

At the temperature 540 °C, The SEM image (Fig. 4b) of the wire pyrolysed reveals an almost smooth surface, indicating

minimal oxidation of the copper. The EDS mapping results (Fig. 5b) show a higher first peak of copper compared to the incinerated wire, suggesting that most of the copper remained in its metallic form. The low oxygen value in this EDS spectrum suggests a

controlled atmosphere during pyrolysis, favoring the reduction of copper oxidation. Pyrolysis appears to be an effective method for cable treatment, facilitating optimal copper recovery and minimising losses due to oxidation.

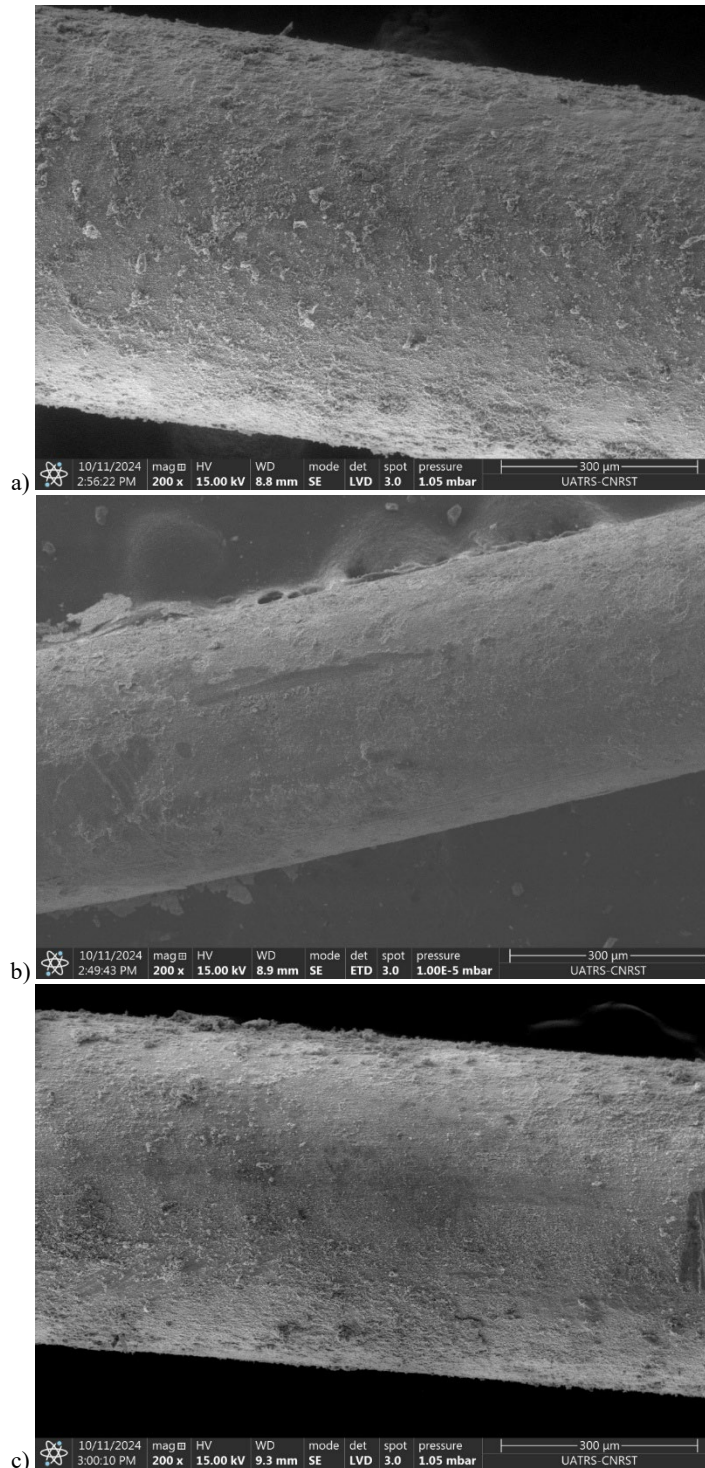


Fig. 4. SEM Pyrolysis products images: a) T=500° C, b) T=540° C, c) T=600° C

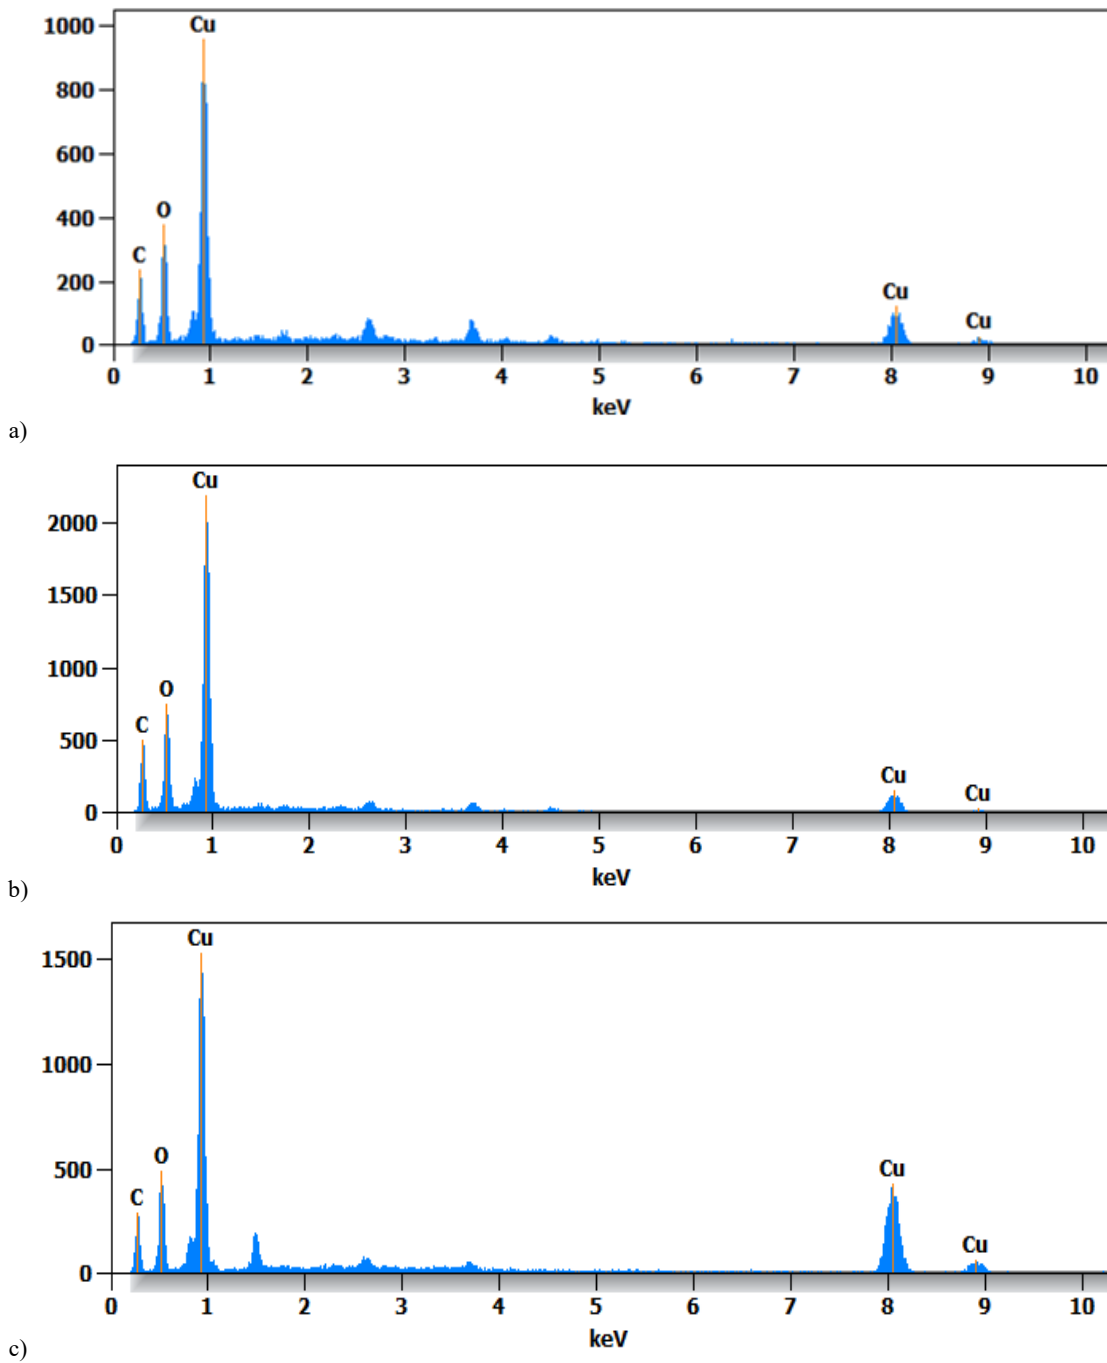


Fig. 5. EDS Pyrolysis products results: a) T=500° C, b) T=540° C, (c)T=600°C

At the same temperature, The SEM image (Fig.6a) of the incinerated wire reveals a rough texture, characterized by the presence of aggregates and particles on the surface. EDS spectre results (Fig.6b) show that the cable contains not only copper, but

also oxygen and traces of carbon. Additionally, the presence of three copper peaks indicates significant oxidation after incineration, suggesting the formation of copper oxides such as Cu_2O and CuO .

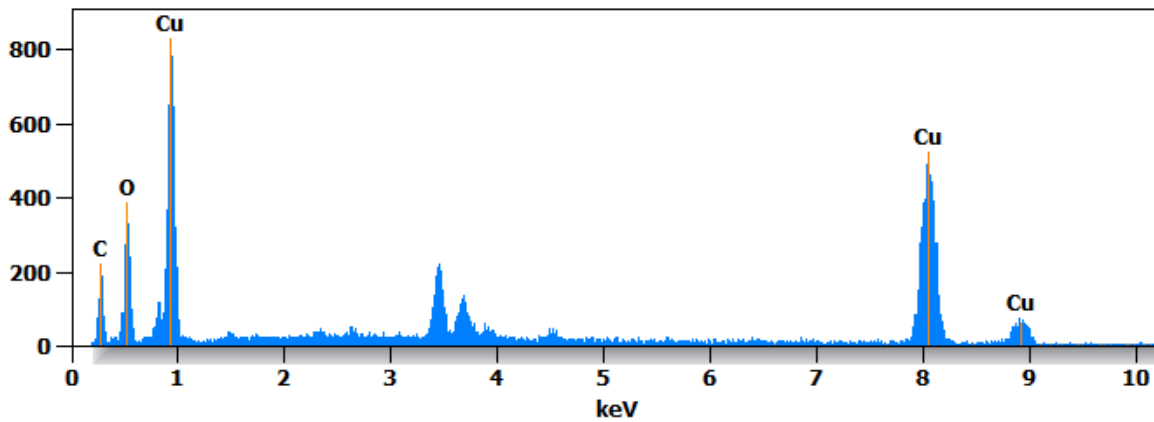
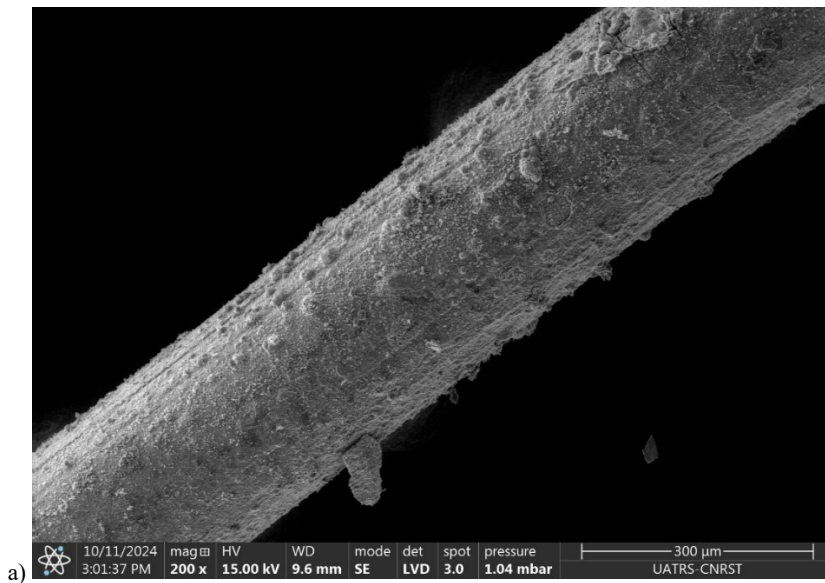


Fig. 6. Incineration product T=540°C: a) SEM image, b) EDS results

The final pyrolysis product, weighing approximately 100 kg, was sent to a foundry in India specializing in the UPCAST process [46]. After analysis, this product was melted to obtain oxygen-free copper rods with a diameter of approximately 8 mm. The average electrical conductivity of these rods, measured with a SigmaScope SMP10 conductivity meter with $\pm 0.5\%$ accuracy, is approximately $(57.4 \pm 0.03) \times 10^6$ S/m (Tab. 3). The % IACS (International

Annealed Copper Standard) value corresponding to this conductivity is $98.2\% \pm 0.03\%$:

$$\% \text{ IACS} = (\sigma_{\text{measure}} / \sigma_{\text{copper}}) \times 100 \text{ with } \sigma_{\text{copper}} = 58.5 \text{ MS/m}$$

$$\text{Incertitude} = 98.2 \times (0.03/100) = 0.03$$

Table 3. Conductivity Measuring Results

	length (mm)	Diameter (mm)	Resistance (Ω)	Rsistivity (Ω .m)	Conductivity (s.m-1)
Sample 1	930	7.88	0.0003344	1.80E-05	57019066
Sample 2	650	7.88	0.0002369	1.80E-05	57256666
Sample 3	300	7.88	0.0001059	1.72E-05	58079725

This result indicates that these rods are of very high quality with IACS > 97% and are suitable for the manufacture of electrical cables [46-47].

With a copper recovery rate of 99.5%, this pyrolysis process remains competitive compared to other processes in later studies [14-36] that require special equipment. This efficiency is attributed

to the use of a special hermetic furnace, allowing for complete decomposition of organic materials and effective metal separation. As a result, this process, capable of handling all types of cables in large quantities, is better suited for the industrial environment.

4. Conclusions

This study presents an effective and sustainable approach to recycling copper wire and cable, including greased ones. The combination of cold and hot treatments, in particular the pyrolysis process in a hermetical furnace, resulted in high metal recovery while limiting toxic emissions. This process successfully decomposed the insulating materials and achieved a maximum copper recovery rate of 99.5%. Furthermore, the copper rods produced through the UPCA process from pyrolysed wire and cable showed excellent electrical conductivity. With a conductivity of 98.2% IACS, these rods can be used in a number of industrial applications, especially in the electrical sector.

Its reduced environmental impact and economic viability make this process particularly suitable for small and medium-sized foundries. It offers a promising solution to the growing need for sustainable copper recycling, contributing to resource conservation and the circular economy.

Acknowledgments

We would like to express our gratitude to everyone at BMC and CNRST, particularly to Mr. Mohamed El Bouji, for their invaluable support throughout this research.

References

- [1] Kumar, H., Kumagai, S., Saito, Y. & Toshiaki Yoshioka, T. (2024). Latest trends and challenges in PVC and copper recovery technologies for End-of-Life thin cables. *Waste Management*. 174, 400-410. <https://doi.org/10.1016/j.wasman.2023.12.012>.
- [2] Japan SDGs Action Forum. (2022). *Summary Report*. Retrieved March 25, 2023, from <https://sdgs.un.org/sites/default/files/2022-07/Event%20Report.pdf>
- [3] Bonnin, M., Azzaro-Pantel, C., Domenech, S. & Villeneuve, J. (2015). Multicriteria optimization of copper scrap management strategy. *Resources, Conservation and Recycling*. 99, 48-62. <http://dx.doi.org/10.1016/j.resconrec.2015.03.013>.
- [4] Wędrychowicz, M., Kurowiak, J., Skrzekut, T. & Noga, P. (2023). Recycling of electrical cables-current challenges and future prospects. *Materials*. 16, 6632, 1-20. <https://doi.org/10.3390/ma16206632>.
- [5] Huang, C.Q. (2012). The development: problems and the new trend of copper conductor processing in China cable industry. *Electric Wire & Cable*. 5, 142-146.
- [6] Piyush, K., Gautam, A., Dayal, H., Bora, A., Patro, C., Sahoo, T. (2015). Selection criteria for usage of aluminum wires in automobile wiring harness. In: 2015 IEEE International Transportation Electrification Conference (ITEC), 14-17 June 2015 (pp. 1-5). <https://doi.org/10.1109/ITEC-India.2015.7386949>.
- [7] Trommnau, J., Kühnle, J., Siegert, J., Inderka, R. & Bauernhansl, T. (2019). Overview of the state of the art in the production process of automotive wire harnesses, current research and future trends. *Procedia CIRP*. 81, 387-392. <https://doi.org/10.1016/j.procir.2019.03.067>.
- [8] Arslan, F., Celik, C. & Arslan, C. (2019). Recycling of waste electrical cables. *Material Science & Engineering International Journal*. 3(4), 107-111. DOI:10.15406/mseij.2019.03.00099.
- [9] Liquan L, Gongqi Liu, Dean Pan, & Wei Wang, (2015). Overview of the recycling technology for copper-containing cables. *Resources, Conservation & Recycling*. 126, 132-140. DOI:10.1016/j.resconrec.2017.07.024.
- [10] Elshkaki A., Graedel T.E., Ciacci L. & Reck B.K. (2016). Copper demand, supply, and associated energy use to 2050. *Global Environmental Change*. 39, 305-315. <https://doi.org/10.1016/j.gloenvcha.2016.06.006>.
- [11] Conesa, Silvia J.A., Egea, S., Moltó, J., Ortuño, N. & Font, R. (2013). Decomposition of two types of electric wires considering the effect of the metal in the production of pollutants. *Chemosphere*. 91(2), 118-123. <https://doi.org/10.1016/j.chemosphere.2012.11.014>.
- [12] Suresh, S.S., Mohanty, S. & Nayak, S.K. (2017). Composition analysis and characterization of waste polyvinyl chloride (PVC) recovered from data cables. *Waste Management*. 60, 100-111. DOI:10.1016/j.wasman.2016.08.033.
- [13] Hagstrom, B. Hampton, R.N., Helmesjo, B. & Hjertberg, T. (2006). Disposal of cables at the "end of life"; some of the environmental considerations. *Feature article*. 22(2), 21-30. DOI: 10.1109/MEI.2006.1618999.
- [14] Zabłocka-Malicka, M., Rutkowski, P. & Szczepaniak, W. (2015). Recovery of copper from PVC multiwire cable waste by steam gasification. *Waste Management*. 46, 488-496. <https://doi.org/10.1016/j.wasman.2015.1008.1001>.
- [15] Buekens, A. & Kefa Cen, K. (2011). Waste incineration, PVC, and dioxins. The 6th International Conference on Combustion, Incineration/Pyrolysis and Emission Control (6th i-CIPEC). *Journal of Material Cycles and Waste Management*. 13, 190-197. DOI 10.1007/s10163-011-0018-9.
- [16] Faragó, T., Špirová, V., Blažeková, P., Lalinská-Voleková, B., Macek, J., Jurkovič, L. Vítková, M. & Hiller, E. (2023). Environmental and health impacts assessment of long-term naturally-weathered municipal solid waste incineration ashes deposited in soil—old burden in Bratislava city, Slovakia. *Heliyon*. 9(3), e13605, 1-18. <https://doi.org/10.1016/j.heliyon.2023.e13605>.
- [17] Youcai, Z. (2017). *Pollution control and resource recovery:municipal solid wastes incineration*. Oxford, UK: Butterworth-Heinemann. <https://doi.org/10.1016/C2016-0-02152-6>.
- [18] Sobotova, L., Badida, M., Dzuro, T. (2019). Analysis of selected technologies of cable Recycling. In 2019 International Council on Technologies of Environmental Protection (ICTEP), 23-25 October 2019 (pp. 234-239). Starý

- Smokovec, Slovakia. DOI:10.1109/ICTEP48662. 2019.8968967.
- [19] Sanritsu Machine Industry Co., Ltd. (2023). *Waste Wire & Cable Recycling Machines*. Retrieved August 20, 2024, from <https://www.sanritsu-machine.com/en/catalog/index.php>.
- [20] Yang, L., Zhen, L., Guilan, T., Ying, L. (2011). Recycling electrically conductive metal and insulating material from cable waste by ultrasonic. In *Third International Conference on Measuring Technology and Mechatronics Automation* (pp. 973-976). DOI:10.1109/ICMTMA.2011.525.
- [21] Sheih, S.W, Tsai, M.S. (2000). Hot water separation process for copper and insulating material recovery from electric cable waste. *Waste Management & Research*. 18(5), 478-484. DOI:10.1034/j.1399-3070.2000.00150.x.
- [22] Ho-Seok Jeon, Chul-Hyun Park, Bong-Gyoo Cho & Jai-Koo Park, (2009). Separation of PVC and rubber from covering plastics in communication cable scrap by tribo-charging. *Separation Science and Technology*. 44(1), 190-202. DOI:10.1080/01614940802286040.
- [23] Park, C.H., Subasinghe, N. & Jeon, H.S. (2015). Separation of covering plastics from particulate copper in cable wastes by induction electrostatic. *Separation Science and Technology*. 56(7), 1140-1143. DOI:10.2320/matertrans.M2015138.
- [24] de Araújo, M.C.P.B., Chaves, A.P., Espinosa, D.C.R., & Tenório, J.A.S. (2008). Electronic scraps-recovering of valuable materials from parallel wire cables. *Waste Management*. 28(11), 2177-2182. <https://doi.org/10.1016/j.wasman.2007.09.019>.
- [25] Feng, Q., Wen, S., Deng, J. & Zhao, W. (2017). Combined DFT and XPS investigation of Enhanced adsorption of sulfide species onto cerussite by surface modification with chloride. *Applied Surface Science*. 425, 8-15. <https://doi.org/10.1016/j.apsusc.2017.07.017>.
- [26] Anastassakis, G.N., Bevilacqua, P. & De Lorenzi, L. (2015). Recovery of residual copper from low- content tailings derived from waste electrical cable treatment. *International Journal of Mineral Processing*. 143, 105-111. <https://doi.org/10.1016/j.minpro.2015.09.011>.
- [27] Lambert, F, Gaydardzhiev, S. Léonard, G., Lewis, G., Bareel, P-F., David & Bastin, D. (2015). Copper leaching from waste electric cables by biohydrometallurgy. *Minerals Engineering*. 76, 38-46. <https://doi.org/10.1016/j.mineng.2014.12.029>.
- [28] Kameda, T., Fukushima, S., Grause, G. & Yoshioka, T. (2013). Metal recovery from wire scrap via a chloride volatilization process: poly(vinyl chloride) derived chlorine as volatilization agent. *Thermochimica Acta*. 562, 65-69. <https://doi.org/10.1016/j.tca.2013.03.012>.
- [29] Hense, P., Reh, K., Franke, M. & Hornung, A. (2015). Pyrolysis of waste electrical and electronic equipment (weee) for recovering metals and energy: previous achievements and current approaches. *Environmental Engineering and Management Journal*. 14(7), 1637-1647. DOI:10.30638/eejm.2015.175.
- [30] Chaala, A., Darmstadt, H. & Roy, C. (1997). Vacuum pyrolysis of electric cable wastes. *Journal of Analytical and Applied Pyrolysis*. 39(1), 79-96. [https://doi.org/10.1016/S0165-2370\(96\)00964-3](https://doi.org/10.1016/S0165-2370(96)00964-3).
- [31] Rong-Hua Ma, Yi-Chang Lin, & Chun-Pao Kuo,(2006). The study of thermal pyrolysis mechanisms for chloro organic compounds in electric cable and medical wastes. *Journal of Analytical and Applied Pyrolysis*. 75(2), 245-251. <https://doi.org/10.1016/j.jaap.2005.06.010>.
- [32] Kundariya, N., Mohanty, S.S., Varjani, S., Ngo, H.H., Wong, J.W.C., Taherzadeh, M., Chang, J.-S., Ng, H.Y., Kim, S.-H. & Bui, X.-T. (2021). A review on integrated approaches for municipal solid waste for environmental and economical relevance: Monitoring tools, technologies, and strategic innovations. *Bioresource Technology*. 342(4), 125982, 1-11. <https://doi.org/10.1016/j.biortech.2021.125982>.
- [33] Mersiowsky, I. (2002). Long-term fate of PVC products and their additives in landfills. *Progress in Polymer Science*. 27(10), 2227-2277. [https://doi.org/10.1016/S0079-6700\(02\)00037-0](https://doi.org/10.1016/S0079-6700(02)00037-0).
- [34] Rambabu, U., Balaram, V., Ratheesh, R., Chatterjee, S., Babu, M.K. & Munirathnam, N. (2018). Assessment of hazardous substances in electrical cables: Implementation of RoHS regulations in India. *Journal of Testing and Evaluation*. 33(3), 1930-1941. DOI:10.1520/JTE20160645.
- [35] Aupetit, A. (2021). Overview of the global cable industry—markets and materials. the global cable industry. *The Global Cable Industry: Materials, Markets, Products*. 1-20. DOI:10.1002/9783527822263.ch1.
- [36] Ma, S., Xing, P., Li, H., Wang, C., Hou, X., Cun, Z., Liu, M. & Yan, R. (2023). Recovery of high-grade copper from waste polyester imide enameled wires by pyrolysis and ultrasonic treatment. *Resources, Conservation & Recycling*. 196, 107034, 1-9. DOI:10.1016/j.resconrec.2023.107034.
- [37] Wajima, T. (2022). Pyrolysis behavior of polyvinyl chloride with sodium hydroxide and application to copper recovery from multiwire tinned copper cables. *International Journal of the Society of Materials Engineering for Resources*. 25(1), 70-77. DOI:10.5188/ijmsr.25.70.
- [38] Xu, J., Kumagai, S., Kameda, T., Saito, Y., Takahashi, K., Hayashi, H. & Yoshioka, T. (2019). Separation of copper and polyvinyl chloride from thin waste electric cables: A combined PVC-swelling and centrifugal approach. *Waste Management*. 89, 27-36. DOI:10.1016/j.wasman.2019.03.049.
- [39] Southard, M.Z., & Ahmed, S. (2019). *Perry's Chemical Engineers' Handbook*. McGraw-Hill Education.
- [40] Papanikolaou, K.G. Jiayang Wu, J., Huber, G.W. & Mavrikakis, M. (2023). Mechanistic insights into the pyrolysis of poly (vinyl chloride). *Journal of Polymer Research*. 30(2), 83, 1-16. DOI:10.1007/s10965-023-03439-6.
- [41] Huggett, C., Levin, B.C. (1987). Toxicity of the Pyrolysis and Combustion Products of Poly (Vinyl Chlorides): *A Literature Assessment*. *Fire and materials*. 11, 131-142. https://tsapps.nist.gov/publication/get_pdf.cfm?pub_id=106993.
- [42] Horikoshi, S., Hachisuga, N. & Serpone, N. (2024). Recycling of e-waste power cables using microwave-induced pyrolysis – process characteristics and facile recovery of copper metal. *RSC Advances*. 14(41), 29955-29964. DOI:10.1039/d4ra05602g.
- [43] Cuevas, A.B., Leiva-Candia, D.E. & Dorado, M.P. (2024). An overview of pyrolysis as waste treatment to produce eco-energy. *Energies*. 17(12), 2852, 1-32. DOI: 10.3390/en17122852.

- [44] Pelzer, Q. (2020). *Étude du vieillissement des isolants synthétiques des câbles moyenne tension "HTA"*. Université Grenoble Alpes. France. Retrieved August 15, 2024, from https://theses.hal.science/tel-02628506v1/file/PELZER_2019_archivage.pdf.
- [45] Shihab, N.R., Enab, T.A., Galal, A. & Ghattas, M.S. (2016). Effect of grain size on orange peel in oxygen free copper wire produced by upcast. *International Journal of Scientific and Engineering Research*. 7(9), 1271-127. <https://www.researchgate.net/publication/310844142>.
- [46] Mao, Q., Zhang, Y., Guo, Y. & Zhao, Y. (2021). Enhanced electrical conductivity and mechanical properties in thermally stable fine-grained copper wire. *Communications materials*. 2(1), 1-9. <https://doi.org/10.1038/s43246-021-00150-1>.
- [47] PX Preciment SA. (2024). Retrieved August 20, 2024, from <https://pxgroup.com/sites/default/files/Cu-ETP.pdf>.